Improved, Low-Cost, Durable Fuel Cell Membranes

2007 Hydrogen Program Annual Review

S. Gaboury, M. Foure, J. Goldbach, D. Mountz, J. Yi, T. Zhang (Arkema)
J. E. McGrath (VPI)
K. More (ORNL)

Arkema, Inc.

May 17, 2007

Project ID#: FCP31

This presentation does not contain any proprietary, confidential, or otherwise restricted information

Overview

Proposed Timeline

- Start Date: July 2007
- End Date: July 2010

Budget

- Total Funding
  - DOE: $6,278K
  - Partners: $1,569K

Barriers & 2010 Targets

- Cost
  - $\$20/m^2$
- Durability
  - 5000 hrs (cycling)

Partners

- Arkema:
  - Virginia Polytechnic Institute
  - Oak Ridge National Laboratory
- Johnson Matthey Fuel Cells
- University of Hawaii

Objectives

- Overall

  - Develop a membrane capable of operating at temperatures up to 120°C and ultra-low relative humidity of inlet gases, per DOE targets. A clear road map to attain this goal based on previously developed PVDF/polyelectrolyte blend technology has been devised.

  - Optimize an MEA based on this new membrane that allows full durability characterization under DOE targets conditions.

  - Elucidate ionomer and membrane failure and degradation mechanisms via *ex-situ* and *in-situ* accelerated testing. Develop mitigation strategies for any identified degradation mechanism.

Arkema's Approach

- Polymer blend system to decouple H^+ conductivity from other requirements
  - Kynar® PVDF
    - Engineering thermoplastic
    - High chemical resistance
    - High electrochemical stability
    - Provide mechanical support
  - Polyelectrolyte
    - H^+ conduction
    - Physical properties unimportant
- Robust blending process
  - Applicable for various polyelectrolytes
  - Capable of morphology and physical property control
- Lower cost approach compared to PFSA
  - Kynar® PVDF - commercial product
  - Polyelectrolyte – hydrocarbon based
- Feasibility demonstrated (M31 & M41)

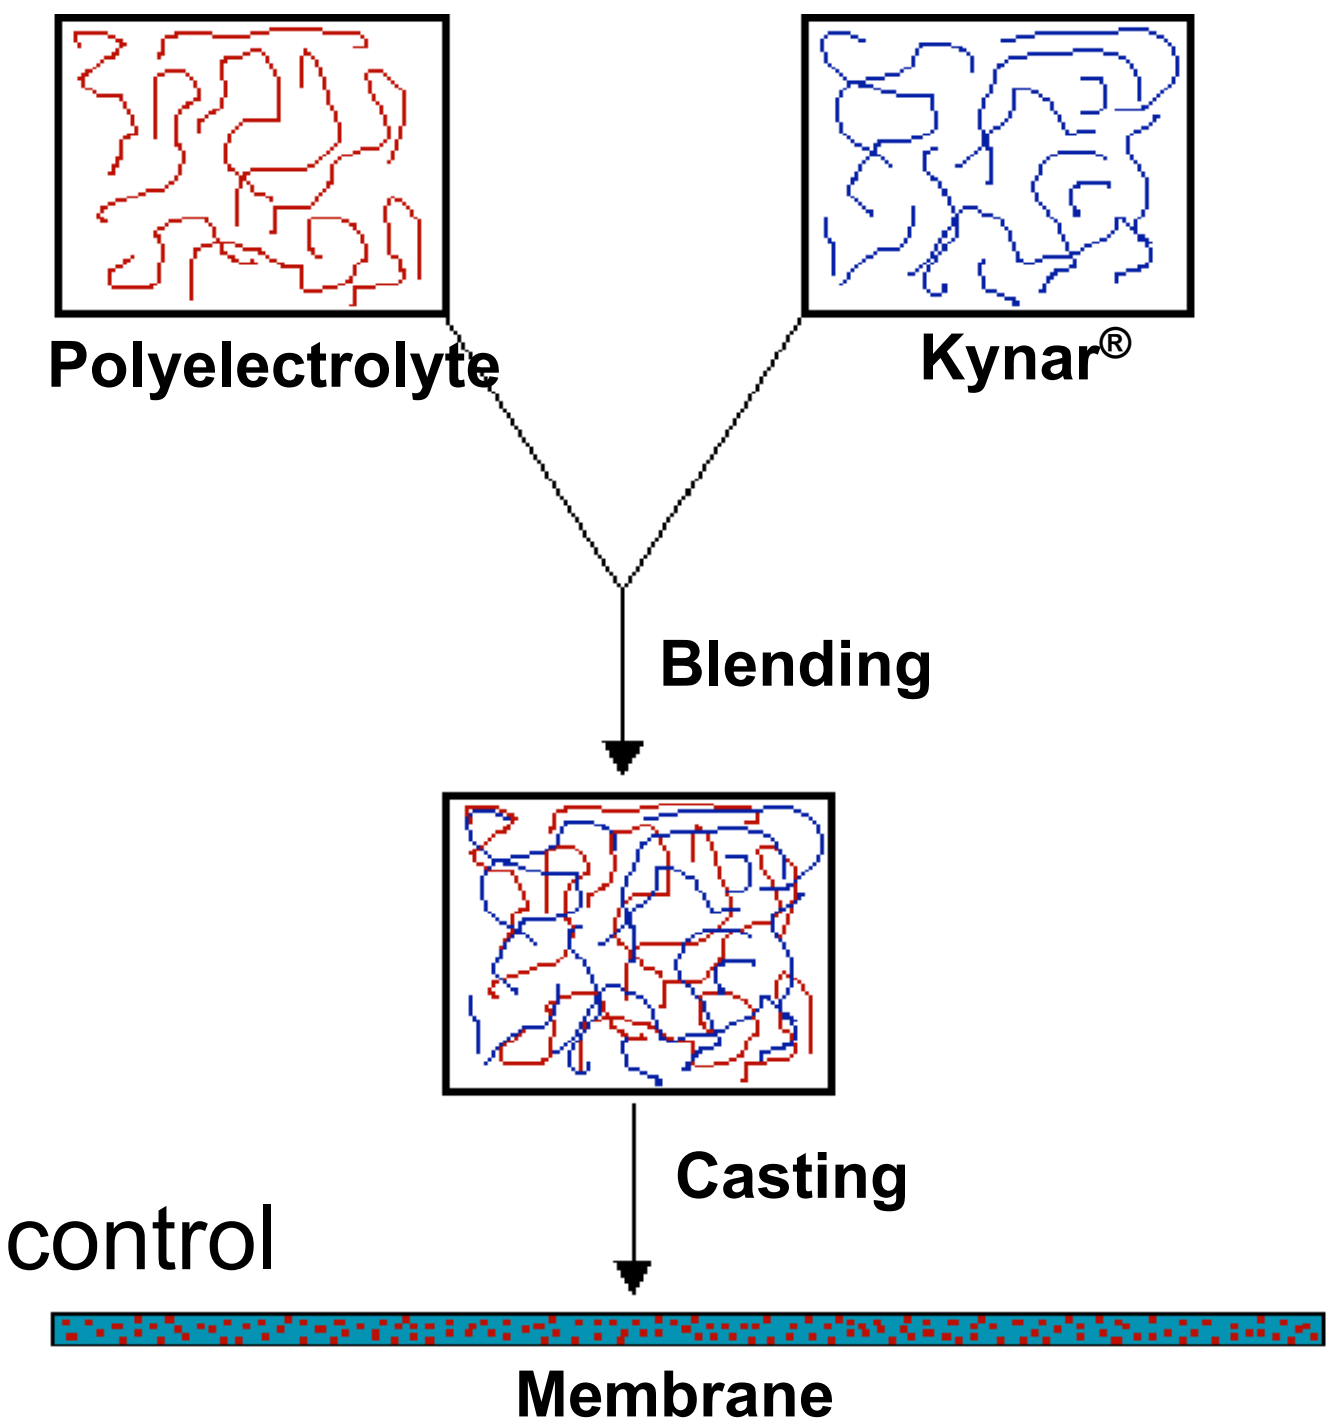

Proposed Project Flow

	I. Polyelectrolyte Development	II. Membrane Development	III. MEA & Fuel Cell Testing	IV. Large Cell Validation
Low RH / High Temp Membrane	• Identify critical go/no go criteria for polyelectrolyte • Prepare and test various polyeletrolyte candidates •Down select polyelectrolyte for membrane evaluations •Arkema & VPI	• Identify critical ex-situ go/no go criteria for membranes • Develop various membrane compositions based on down selected PE and characterize membranes, including morphology • Down select membranes for MEA development • Arkema & ORNL	• Identify critical *in-situ* go/no go criteria, per DOE targets • Develop MEAs optimized for running new membrane under DOE conditions • Conduct EOL testing and accelerated durability • Arkema & Johnson Matthey	• Develop testing protocols • Fabricate large 5 & 7 layer MEAs • Conduct large scale cell testing including BOL & EOL diagnostics • Arkema, Johnson Matthey & U. of HI

I. Polyelectrolyte Development

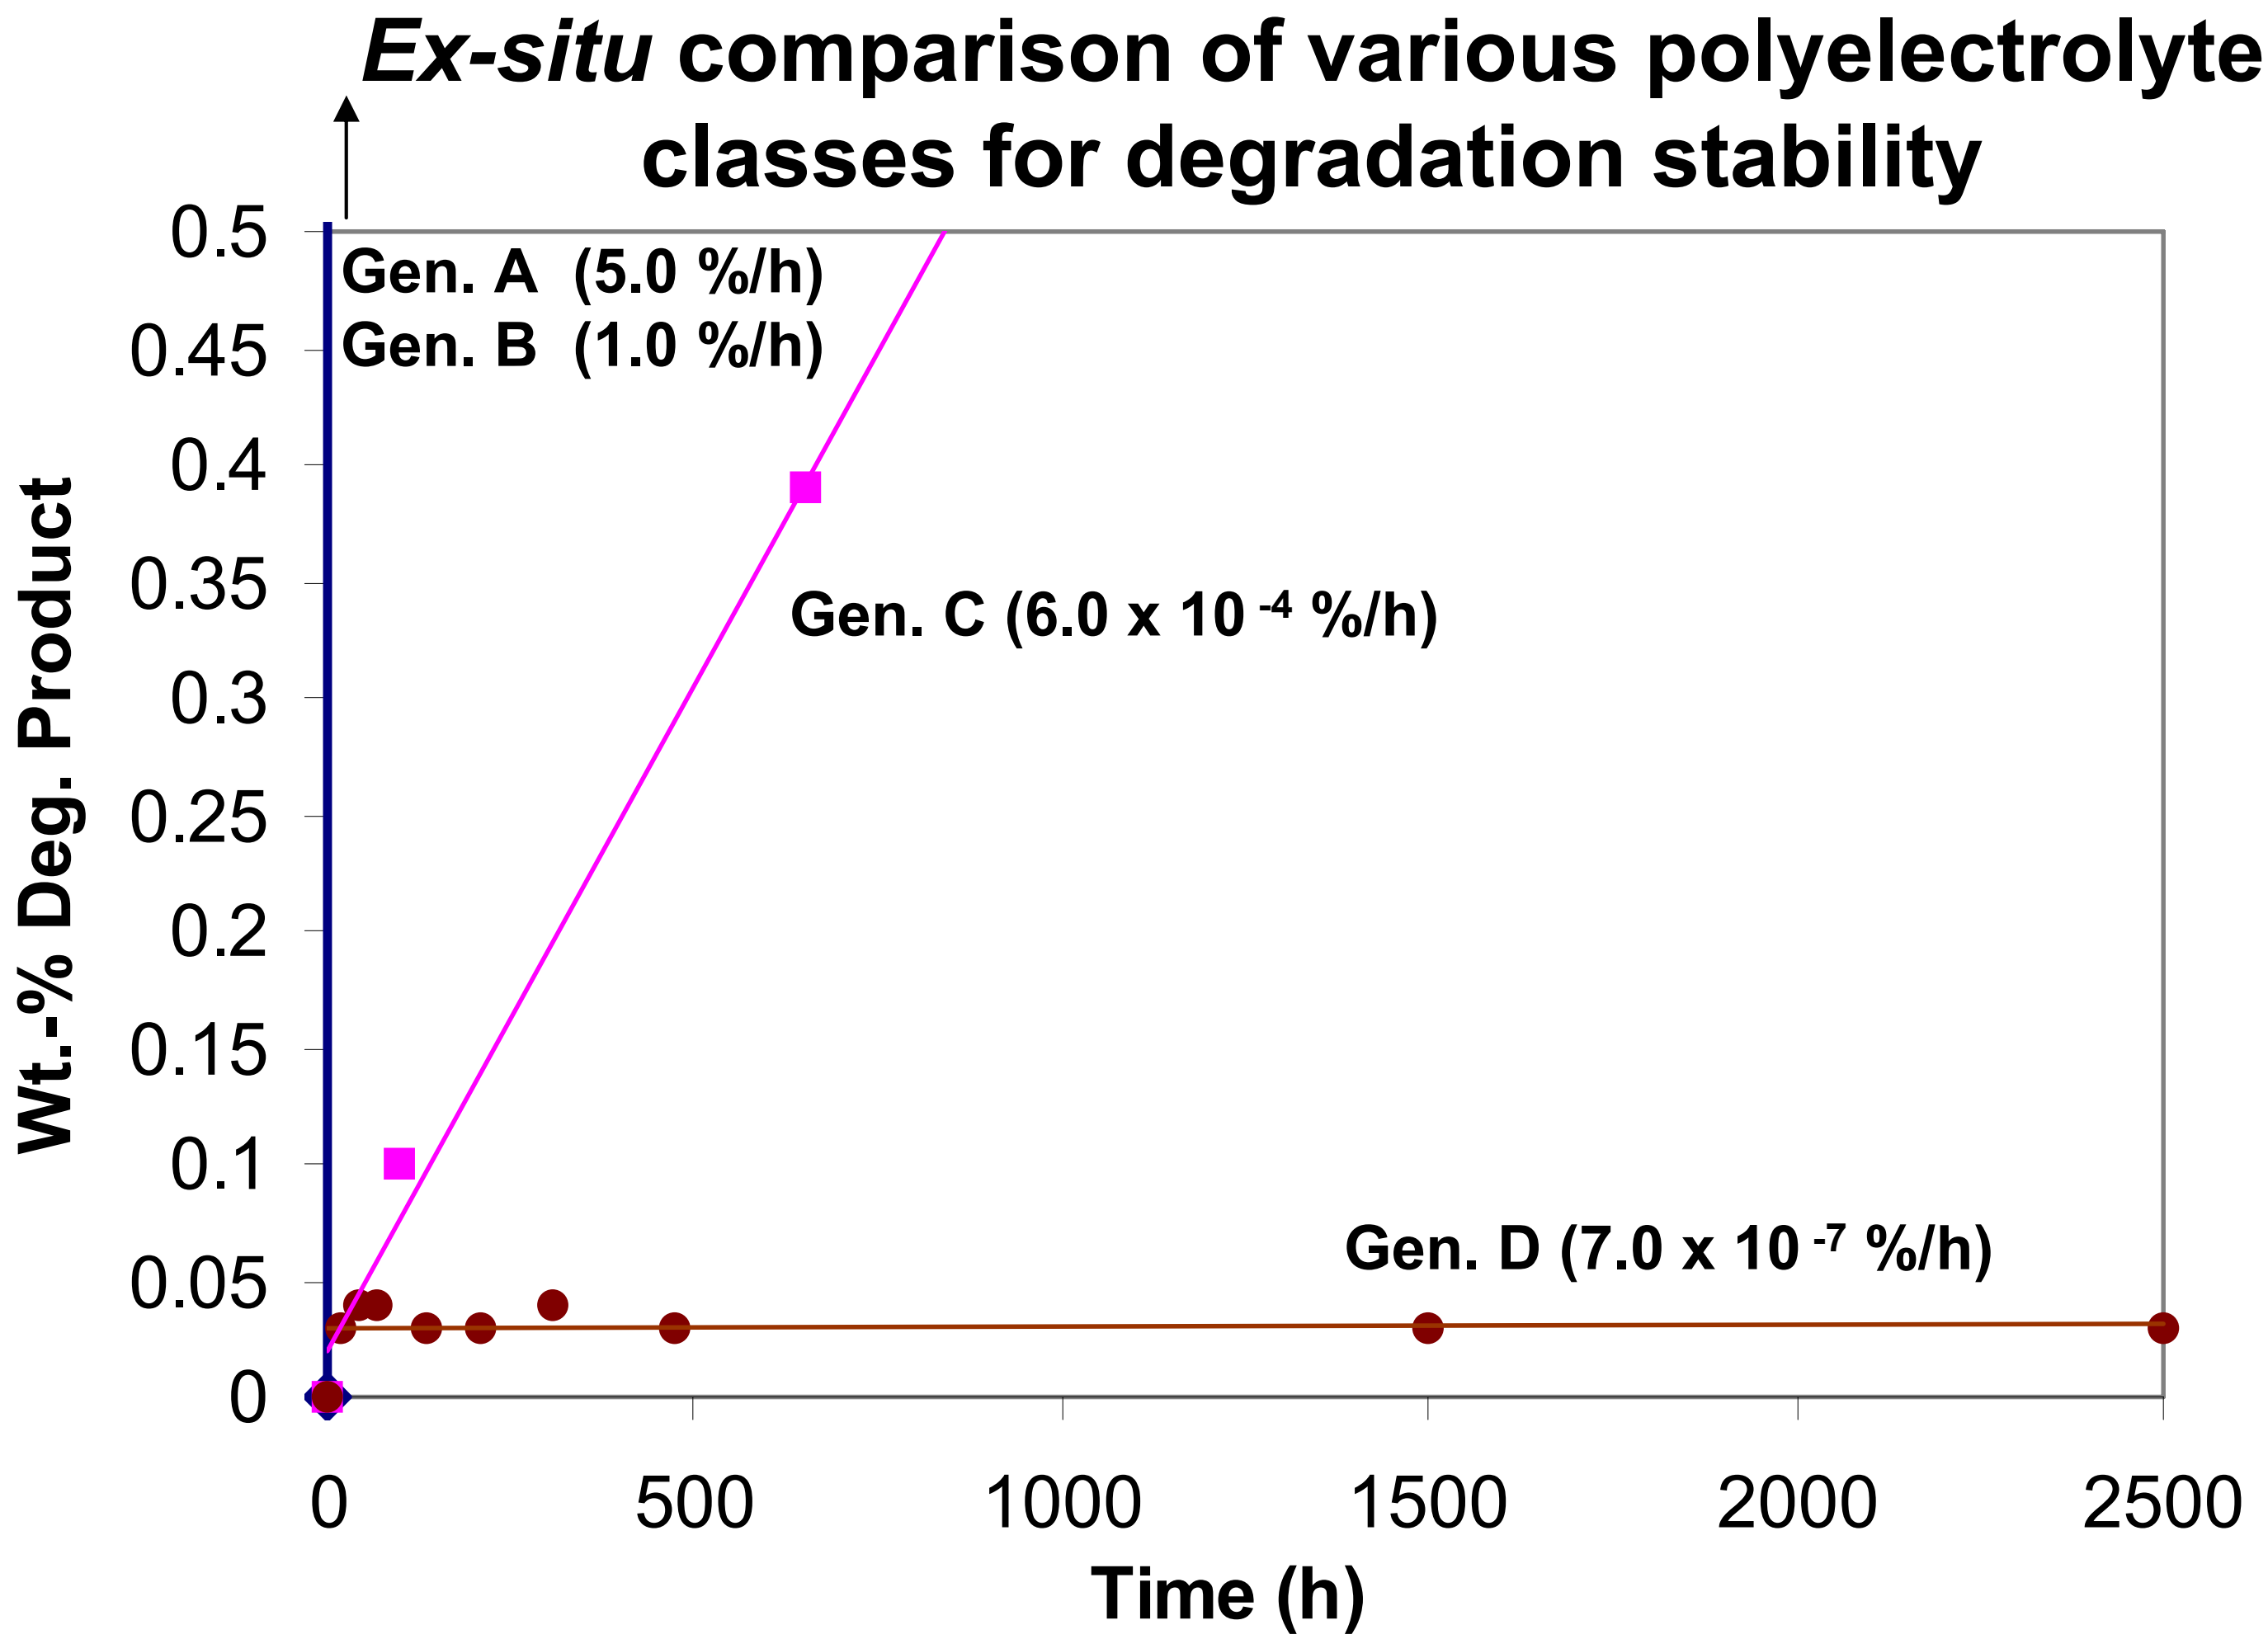

- Generation D polyelectrolyte (used in M41) showed no measurable degradation in our *ex-situ* accelerated testing

Another possible structure class to be evaluated: Poly(arylene Ether Sulfone)s

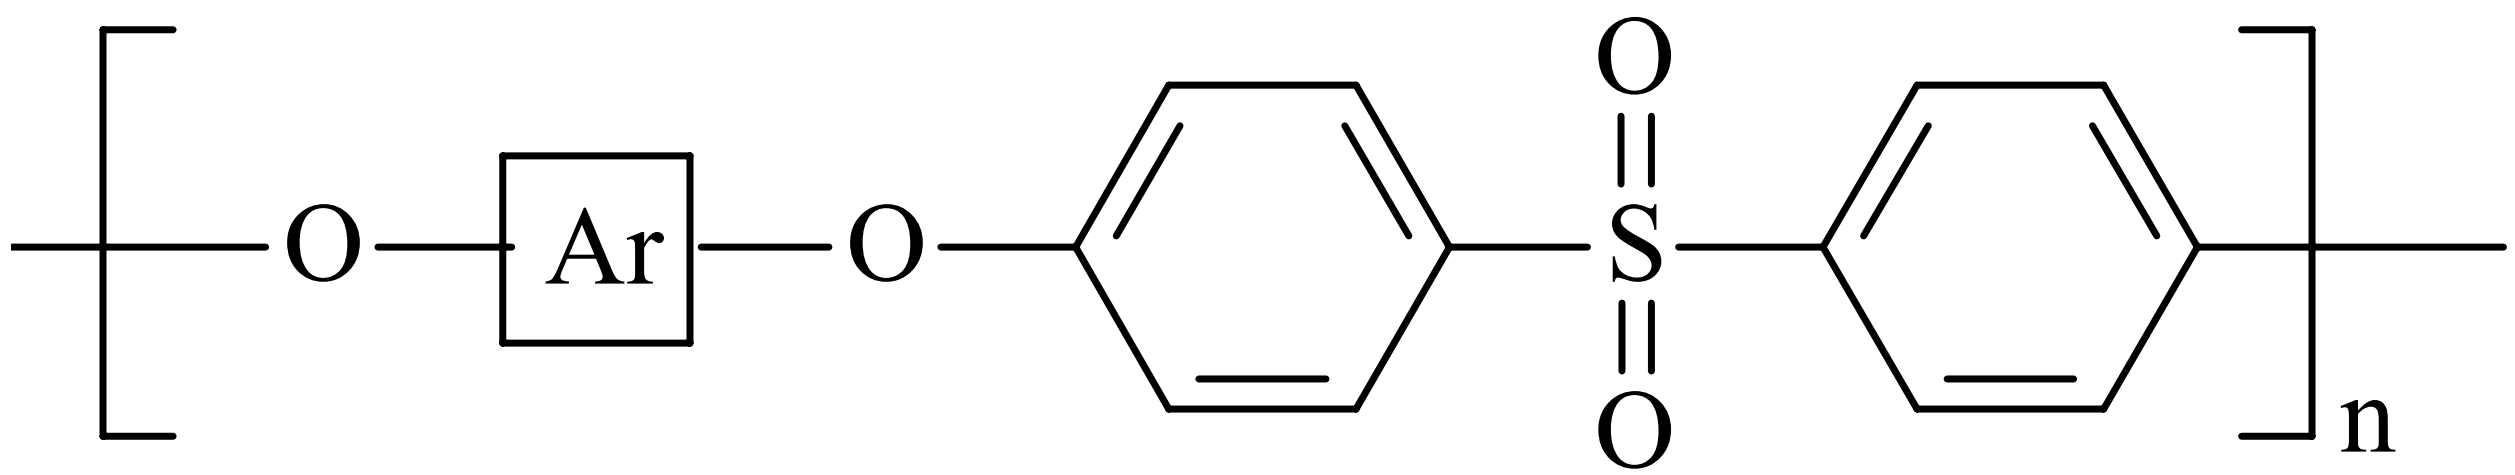

- High thermal stability
- Good stability against acid, bases and oxidants
- Good mechanical properties
- Film-forming, high-performance thermoplastics
- Melt processible
- Several monomers are commercially available

Wang, S. and McGrath, J.E. In: *Polyarylene Ethers*: *A review*, In: *Step Polymerization*, Rogers, M. and Long, T.E., Eds., Wiley, **2003**

ARKEMA

Tailoring of Poly(arylene Ether Sulfone)s

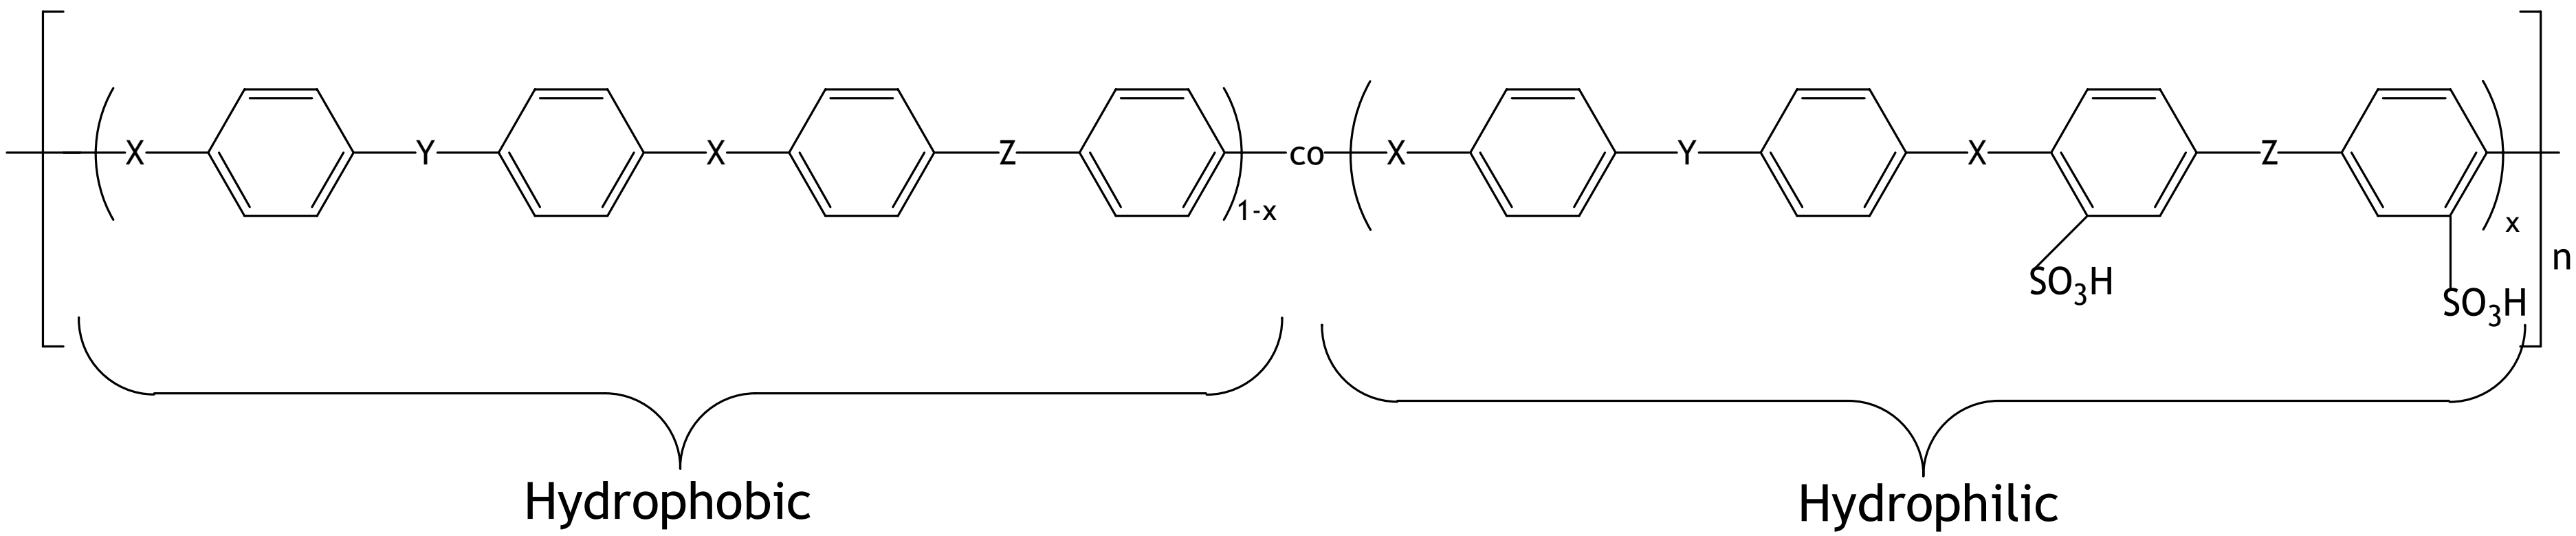

X = O, S

Y = a bond,  ,  , SO_2 , 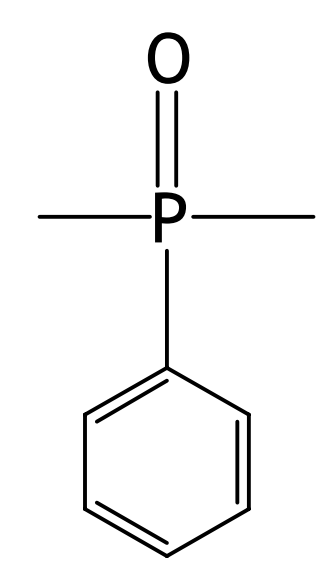

Z = SO_2 ,  , 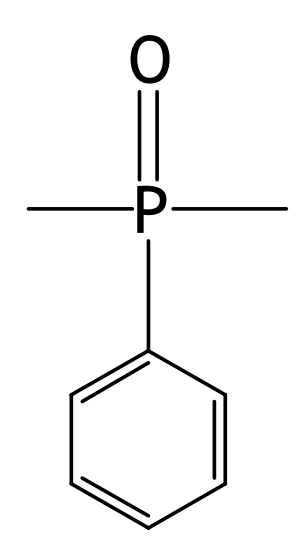

W. Harrison, F. Wang, J. Mecham, V. Bhanu, M. Hill, Y. Kim, and J. E. McGrath, Synthesis of Sulfonated Poly(arylene ether copolymers). J. Poly.Sci. 41, 2264-2276 (2003).

II. Membrane Development

Polyelectrolyte	Conductivity (mS/cm)
• Model materials	
• P(AMPS)	90-120
• Sulfonated Polystyrene	50-90
• Proprietary polyelectrolytes	
• Generation A (M31)	120-150
• Generation B	120-140
• Generation C	60-120
• Generation D (M41)	120 -140

Phase Separated

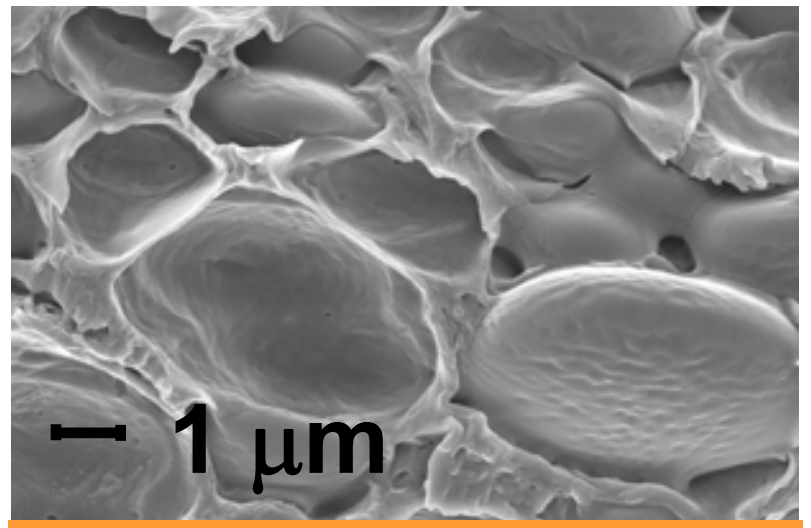

20 - 40 mS/cm

Compatibilized

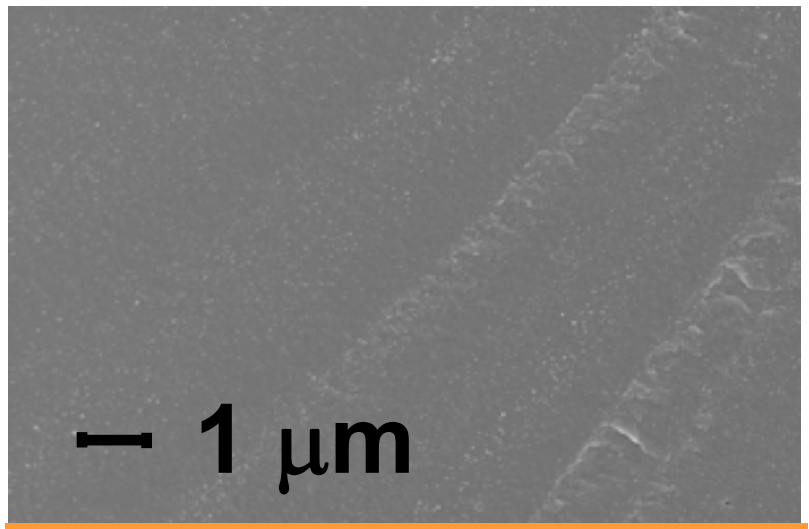

>100 mS/cm

Kynar® PVDF blending process is generally applicable for highly protogenic polymers

ARKEMA

M41 Physical Properties

	Nafion® 111	M41
Dry Thickness (μm)	25	25
Equivalent Weight	1100	800
Density (g/cm^3)	1.8	1.5
Water Uptake (%)	37	60
X,Y Swell (%)	15	20
Thickness Swell (%)	14	10-15
Tensile Stress Break (MPa)	19	27
Elongation (%)	103	95
Tear Strength(lb_f/in)	404	934
Tear Propagation (lb_f)	0.004	0.018

- M41 shows equal/better mechanical properties than Nafion® 111

ARKEMA

M41 Transport Properties

- Equivalent proton Conductivity compared to Nafion®

Proton Conductivity (mS/cm)*

- Superior gas barrier properties than Nafion® membranes

H_2 permeation rate (mA/cm^2)**

* by 4-point in-plane AC measurements in water at 70°C

** by electrochemical method at 80°C with 100% RH

Ex-situ Membrane Chemical Stability

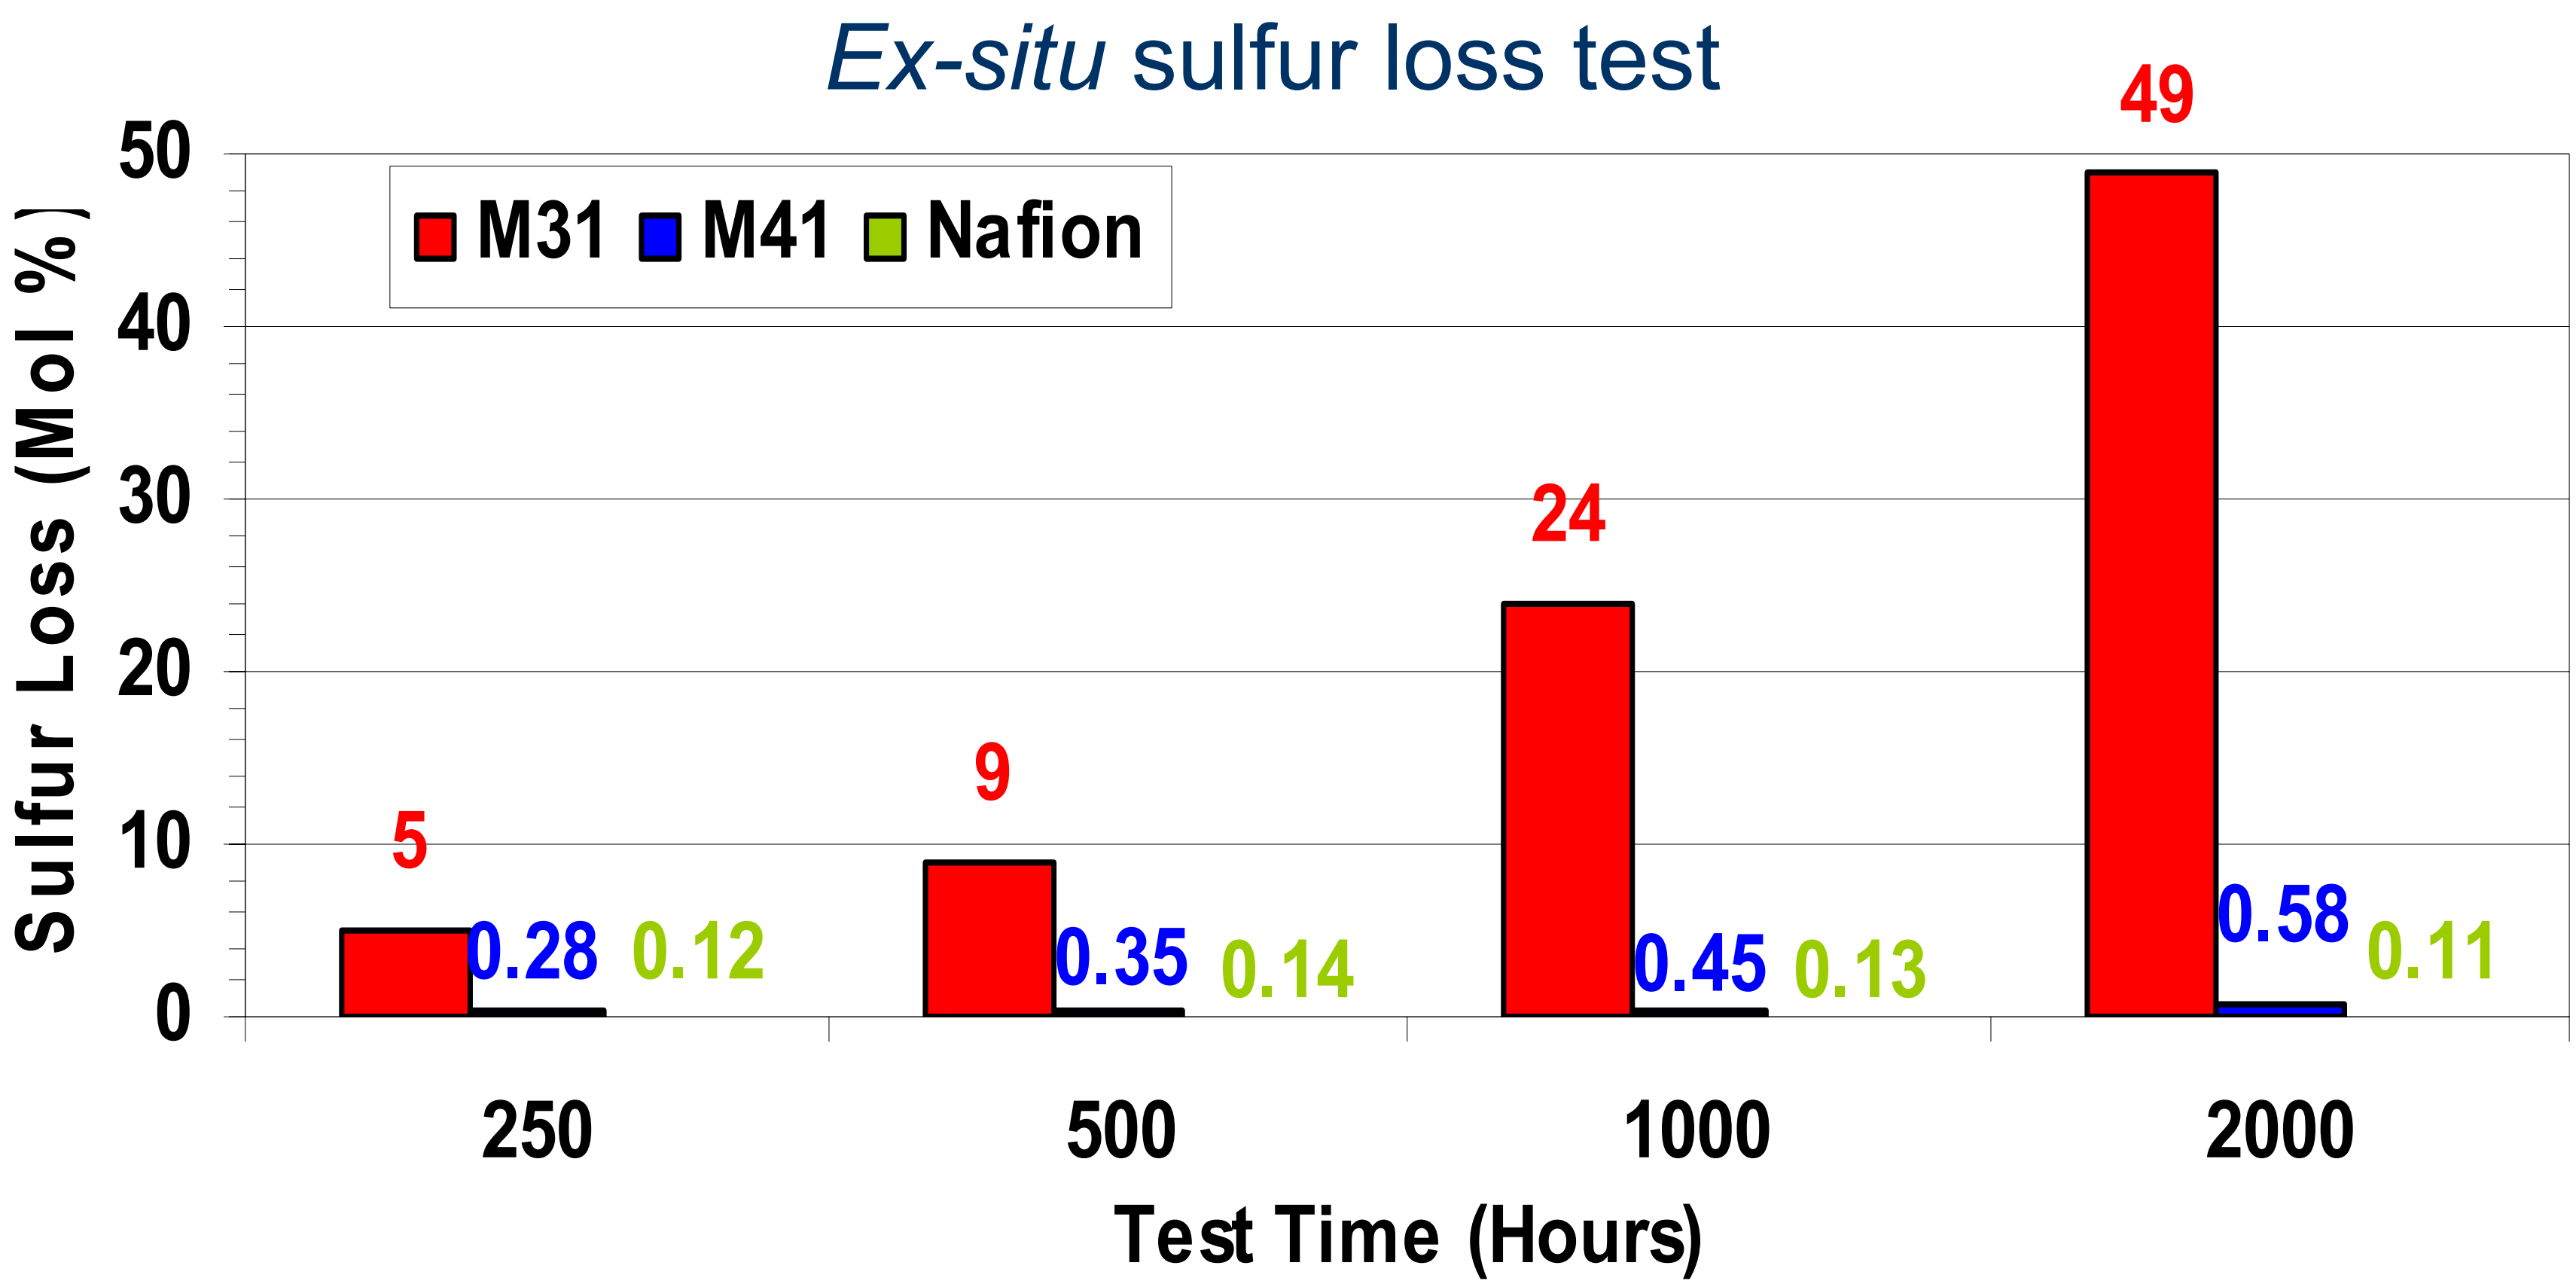

- M41 shows less than 1% sulfur loss over 2000hr

Morphology Characterization: M31 TEM (ORNL)

- ~300 nm-wide striations
  - Possible water diffusion pathways

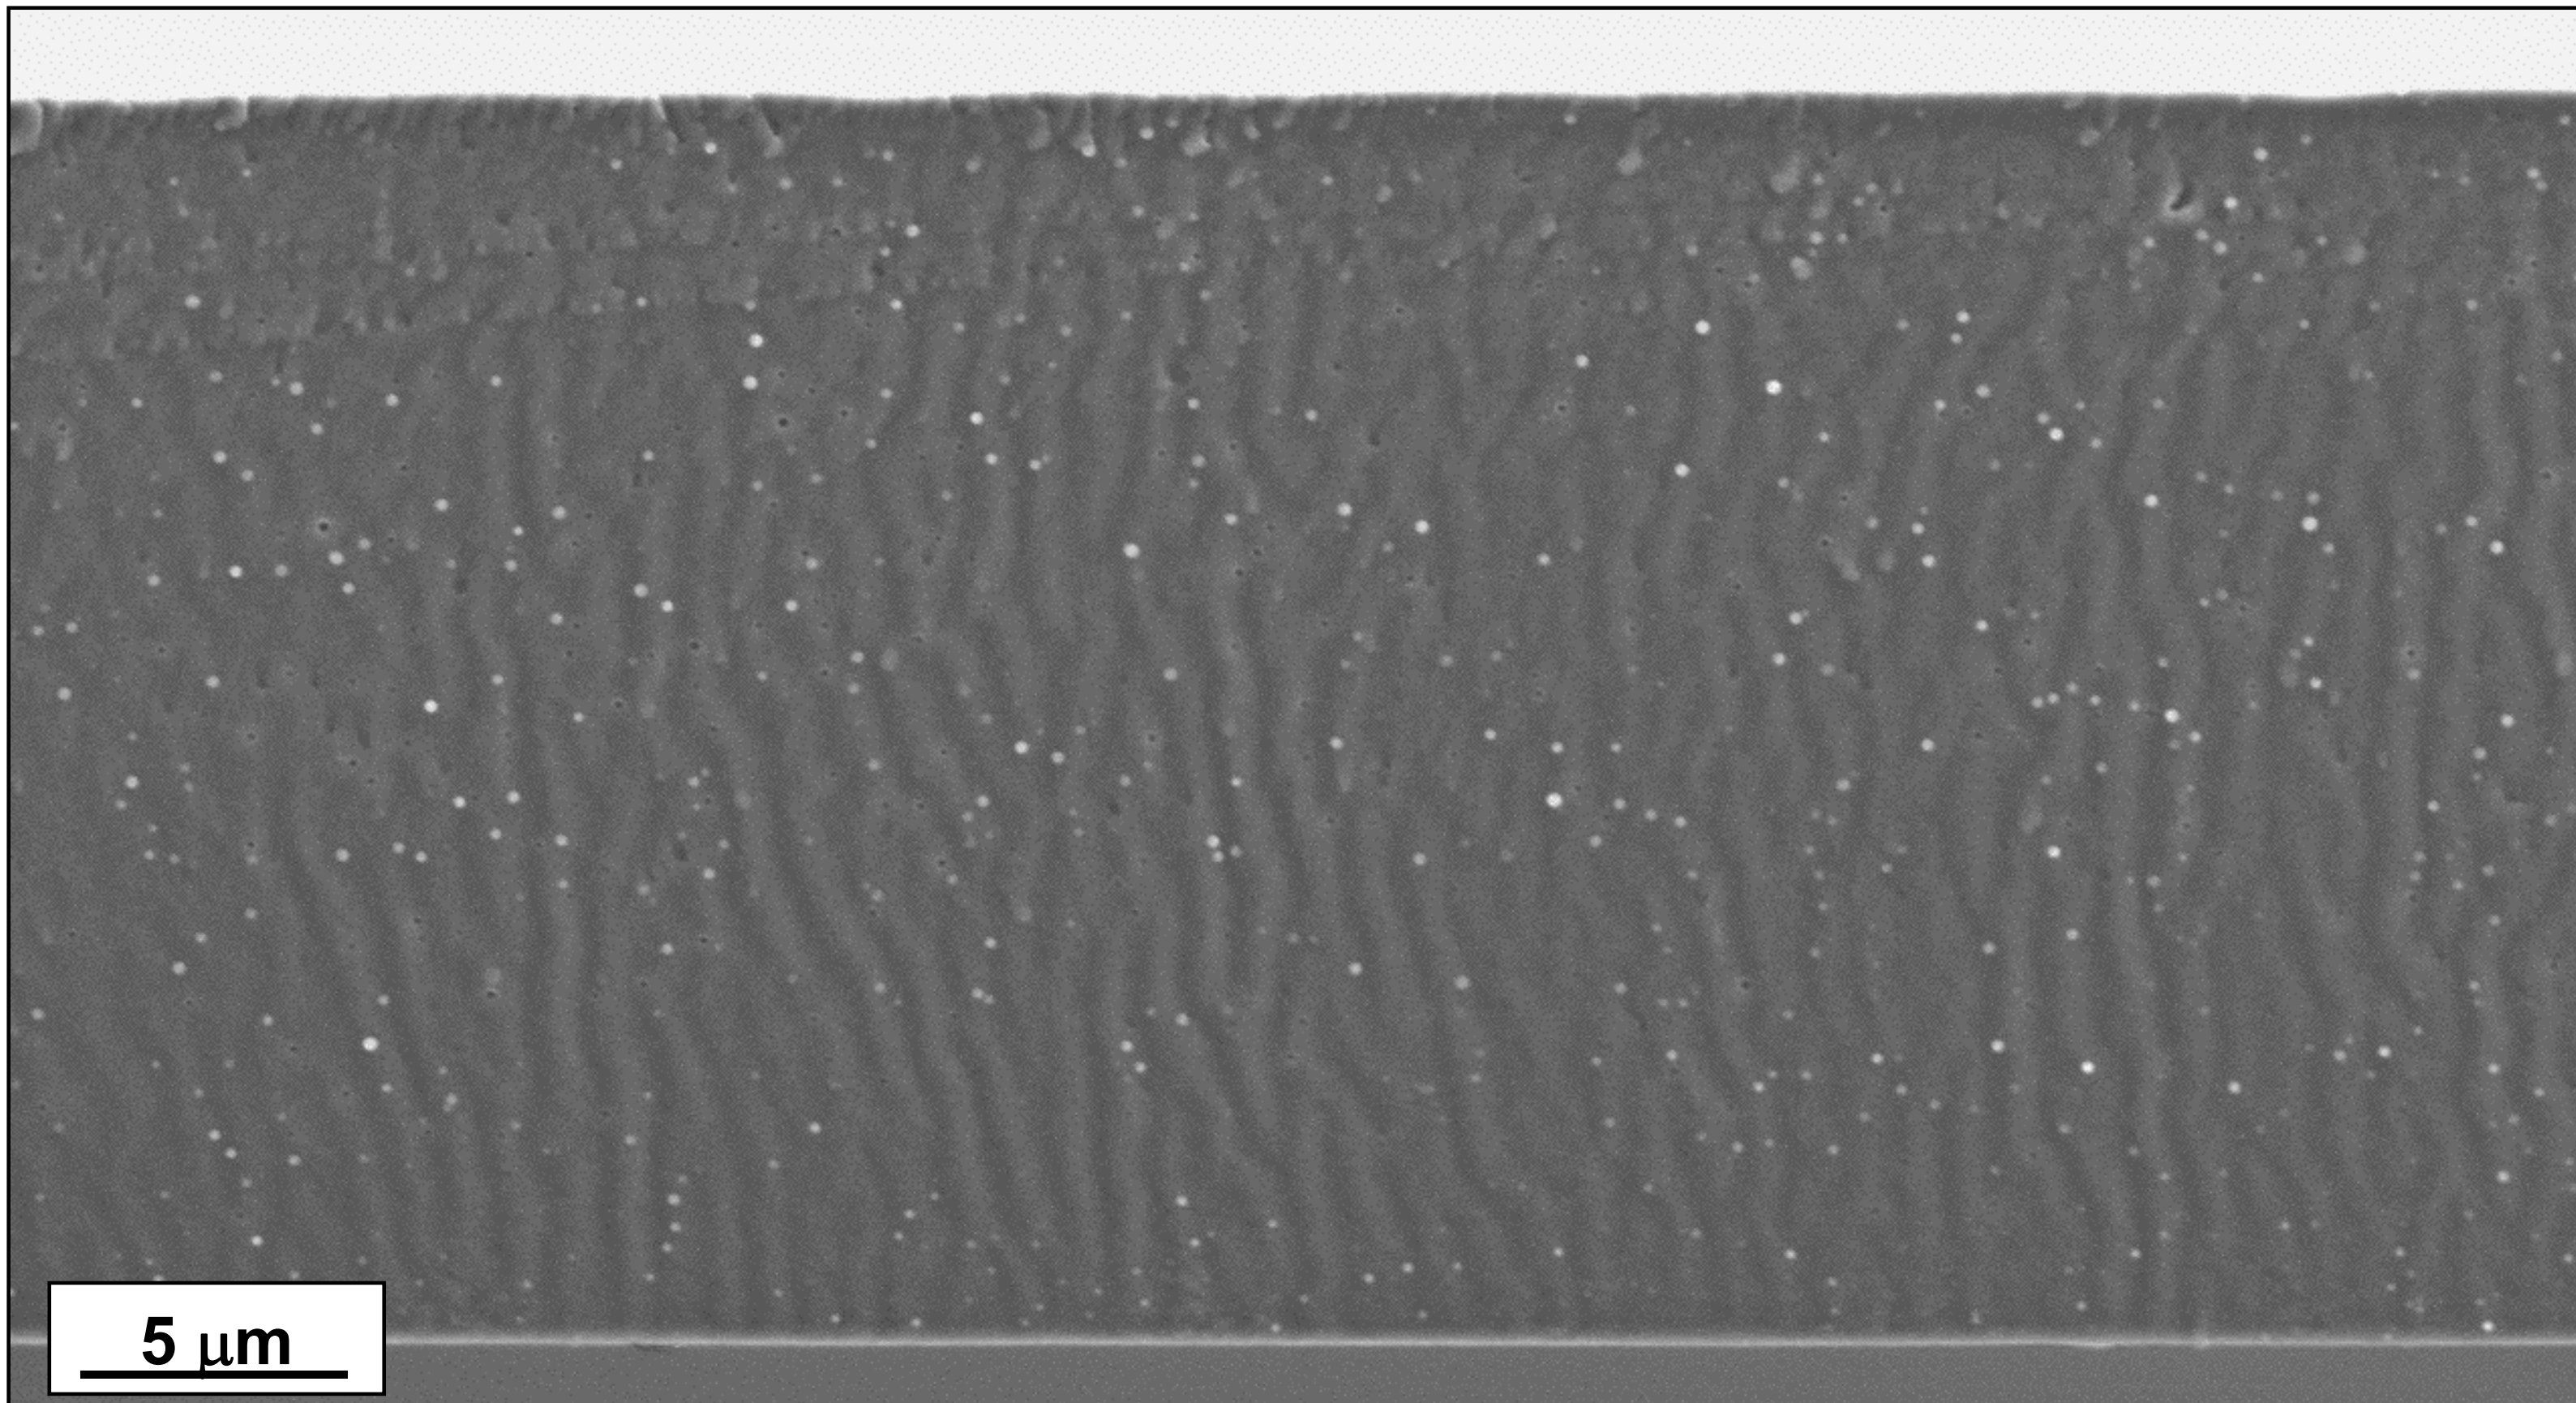

Morphology Characterization: M41 TEM (ORNL)

M41 (early development stage)

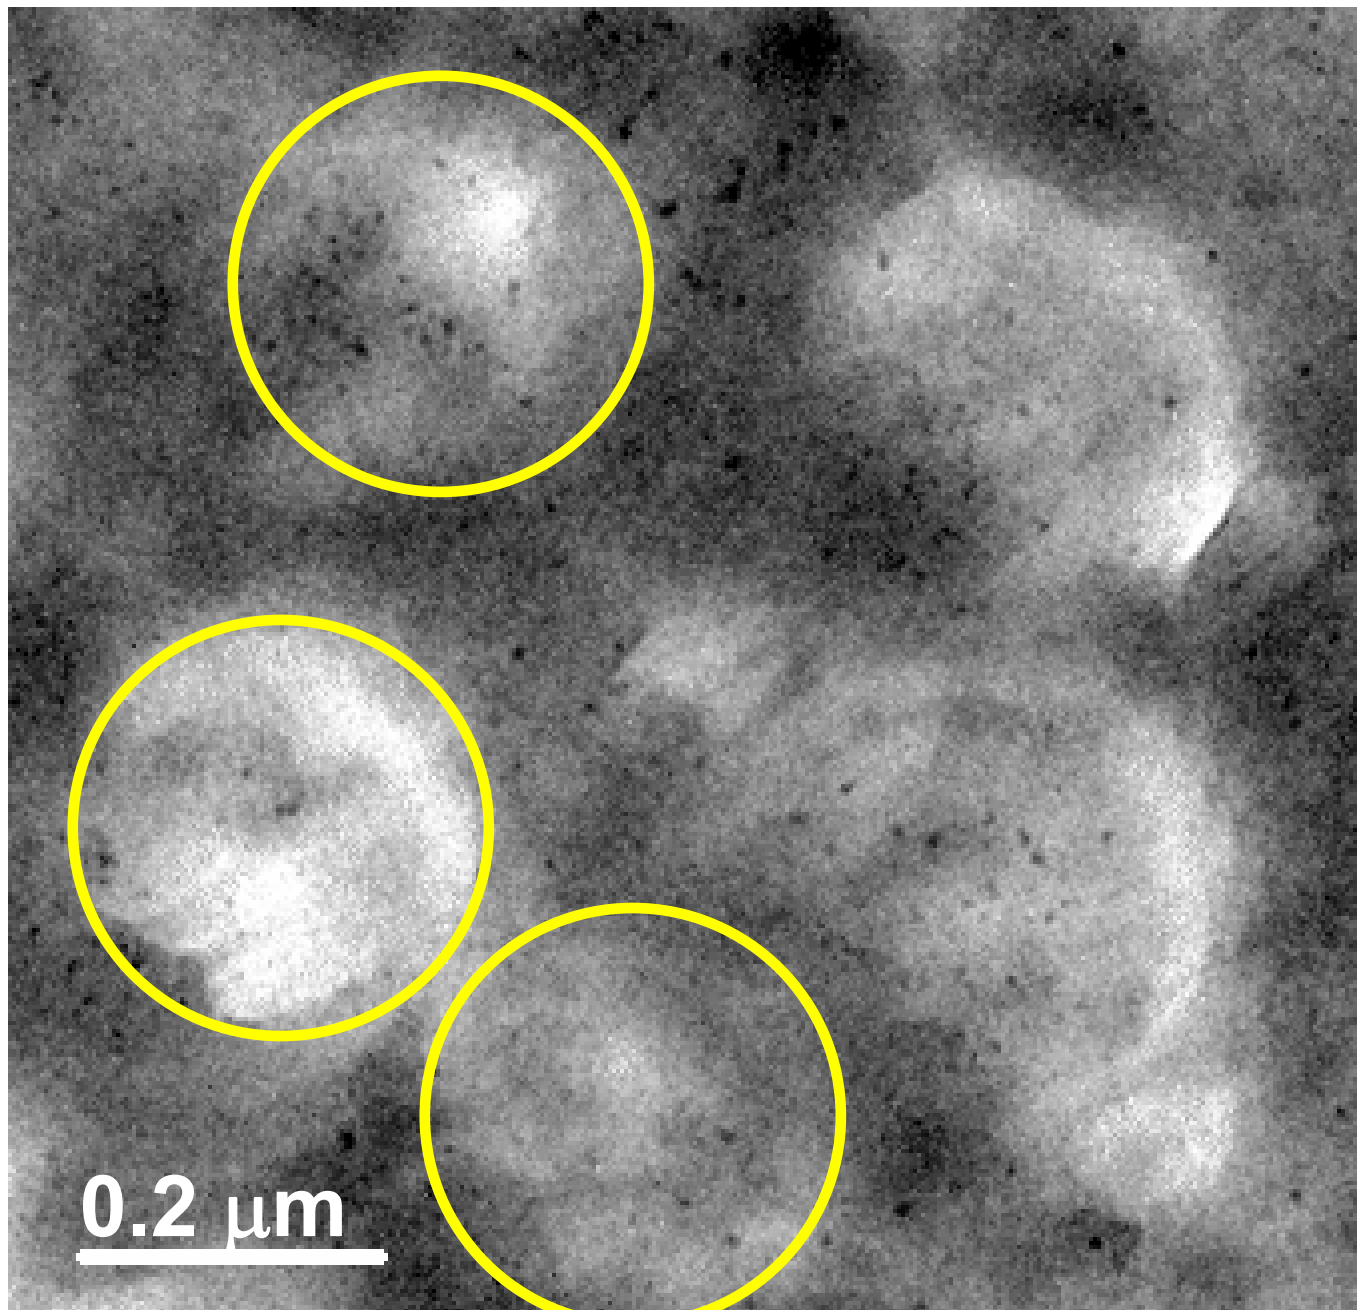

Conductivity = 100 mS/cm

M41 (pilot membrane)

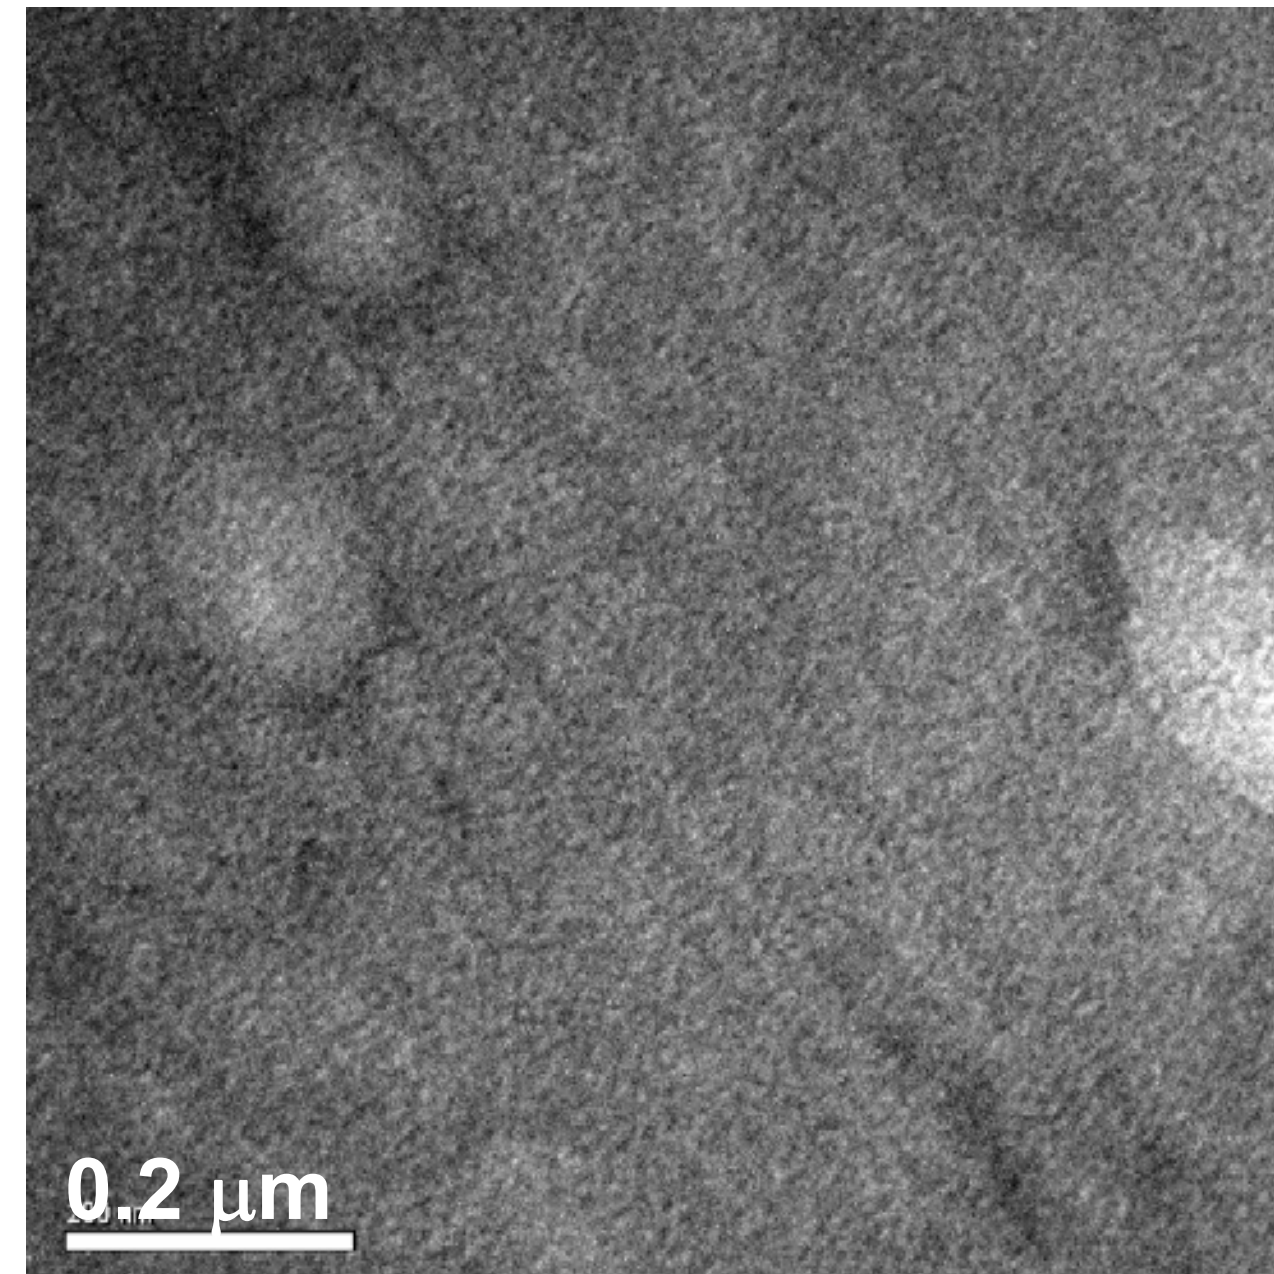

Conductivity = 130 mS/cm

- High-resolution TEM characterization to gain understanding of structure and property

III. MEA & Fuel Cell Testing: M41 Beginning of Life Performance

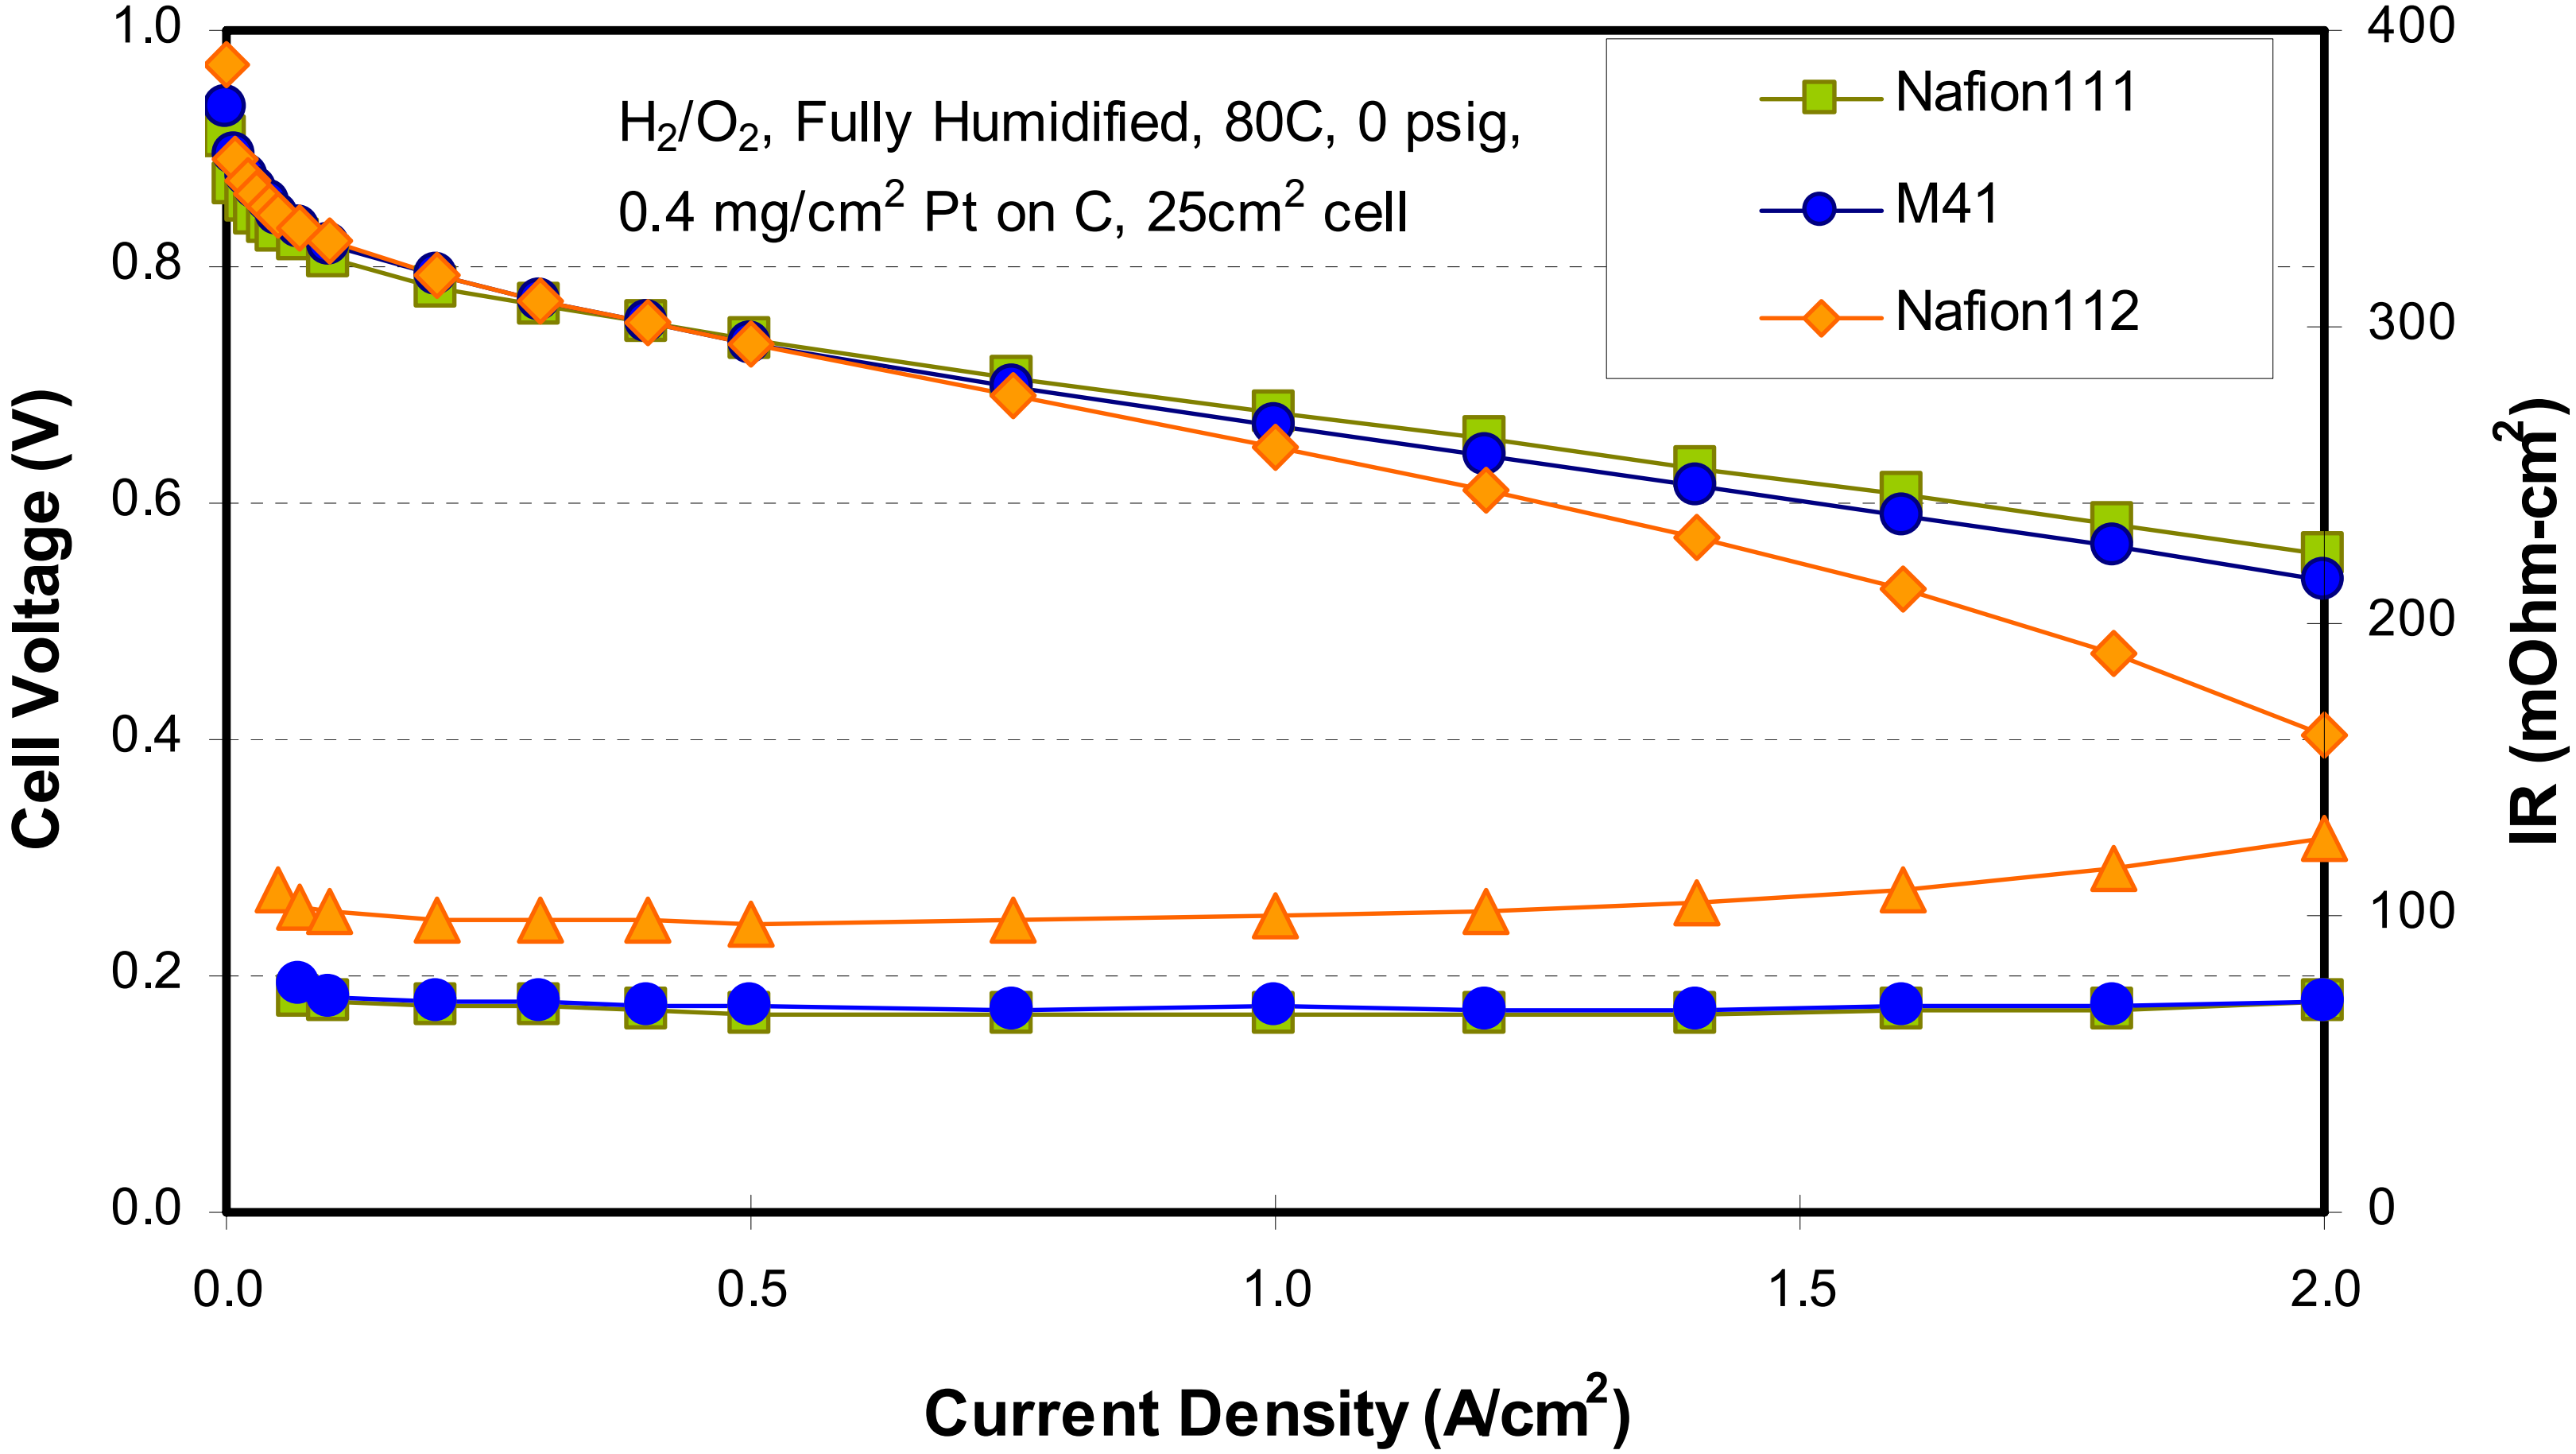

- Comparable in-cell performance to Nafion® 111 demonstrated

M41 OCV Durability: Hydrogen Crossover

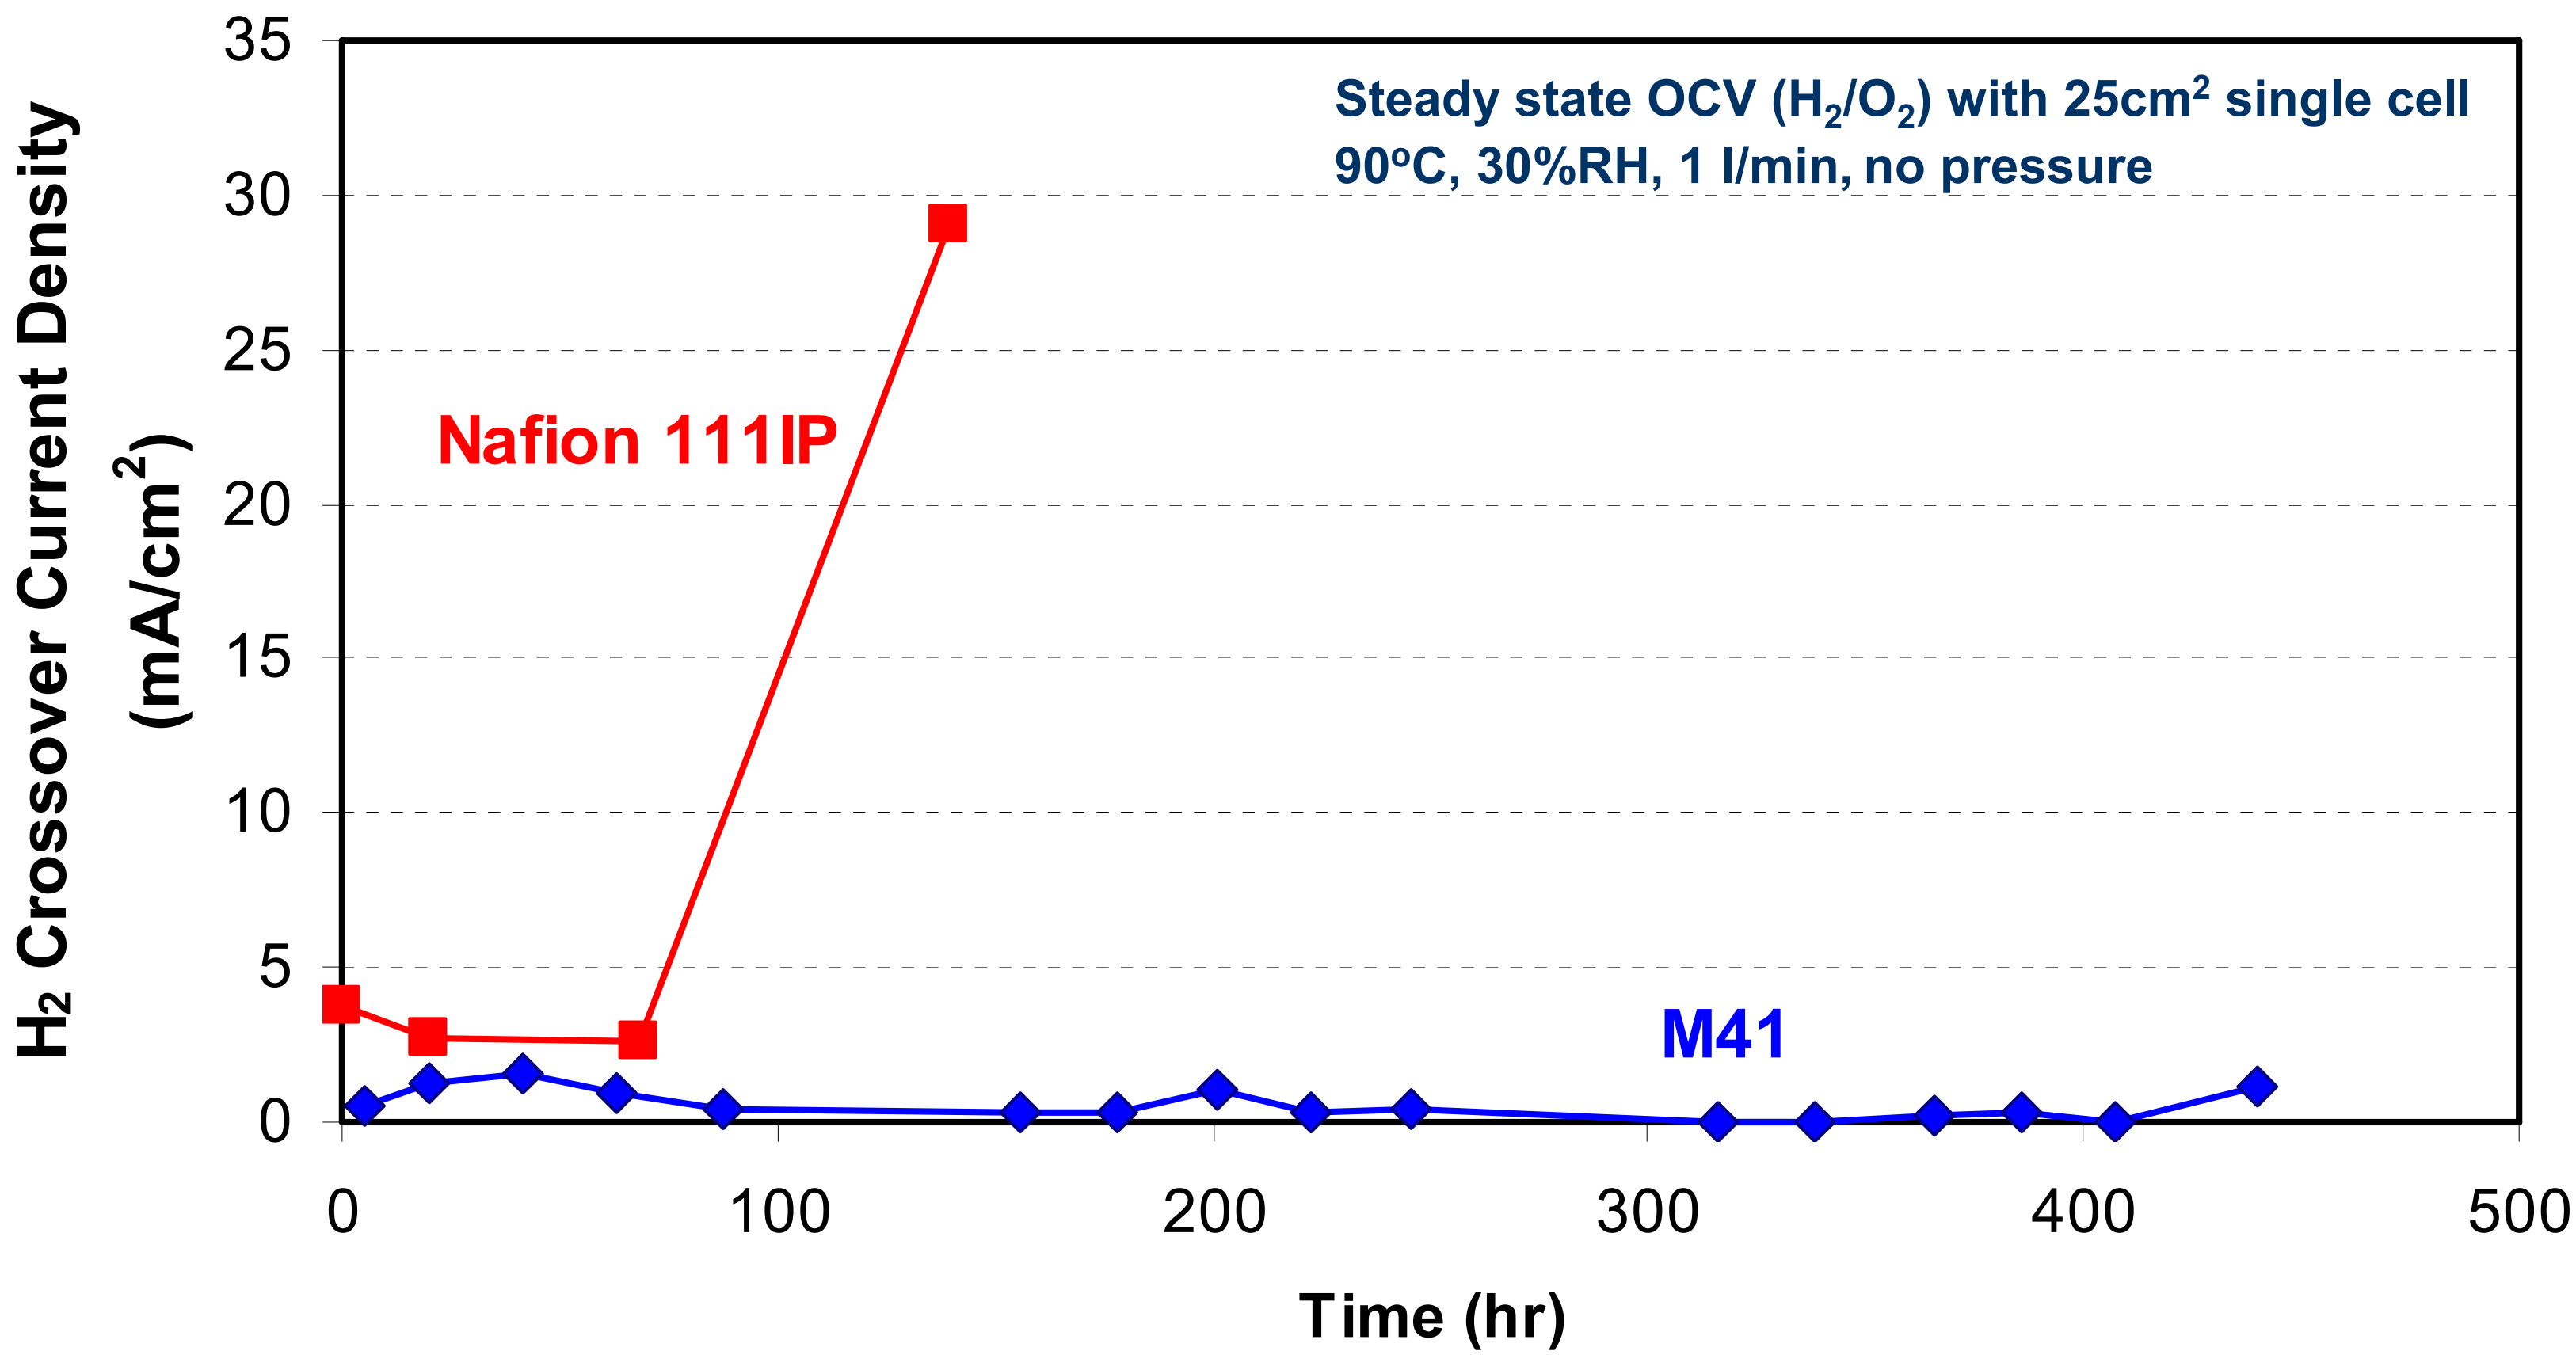

- Nafion® 111IP membranes failed at 100 –150 hrs
- M41 membranes exhibit superior chemical stability in fuel cells

M41 OCV Durability: Effluent Water Analysis

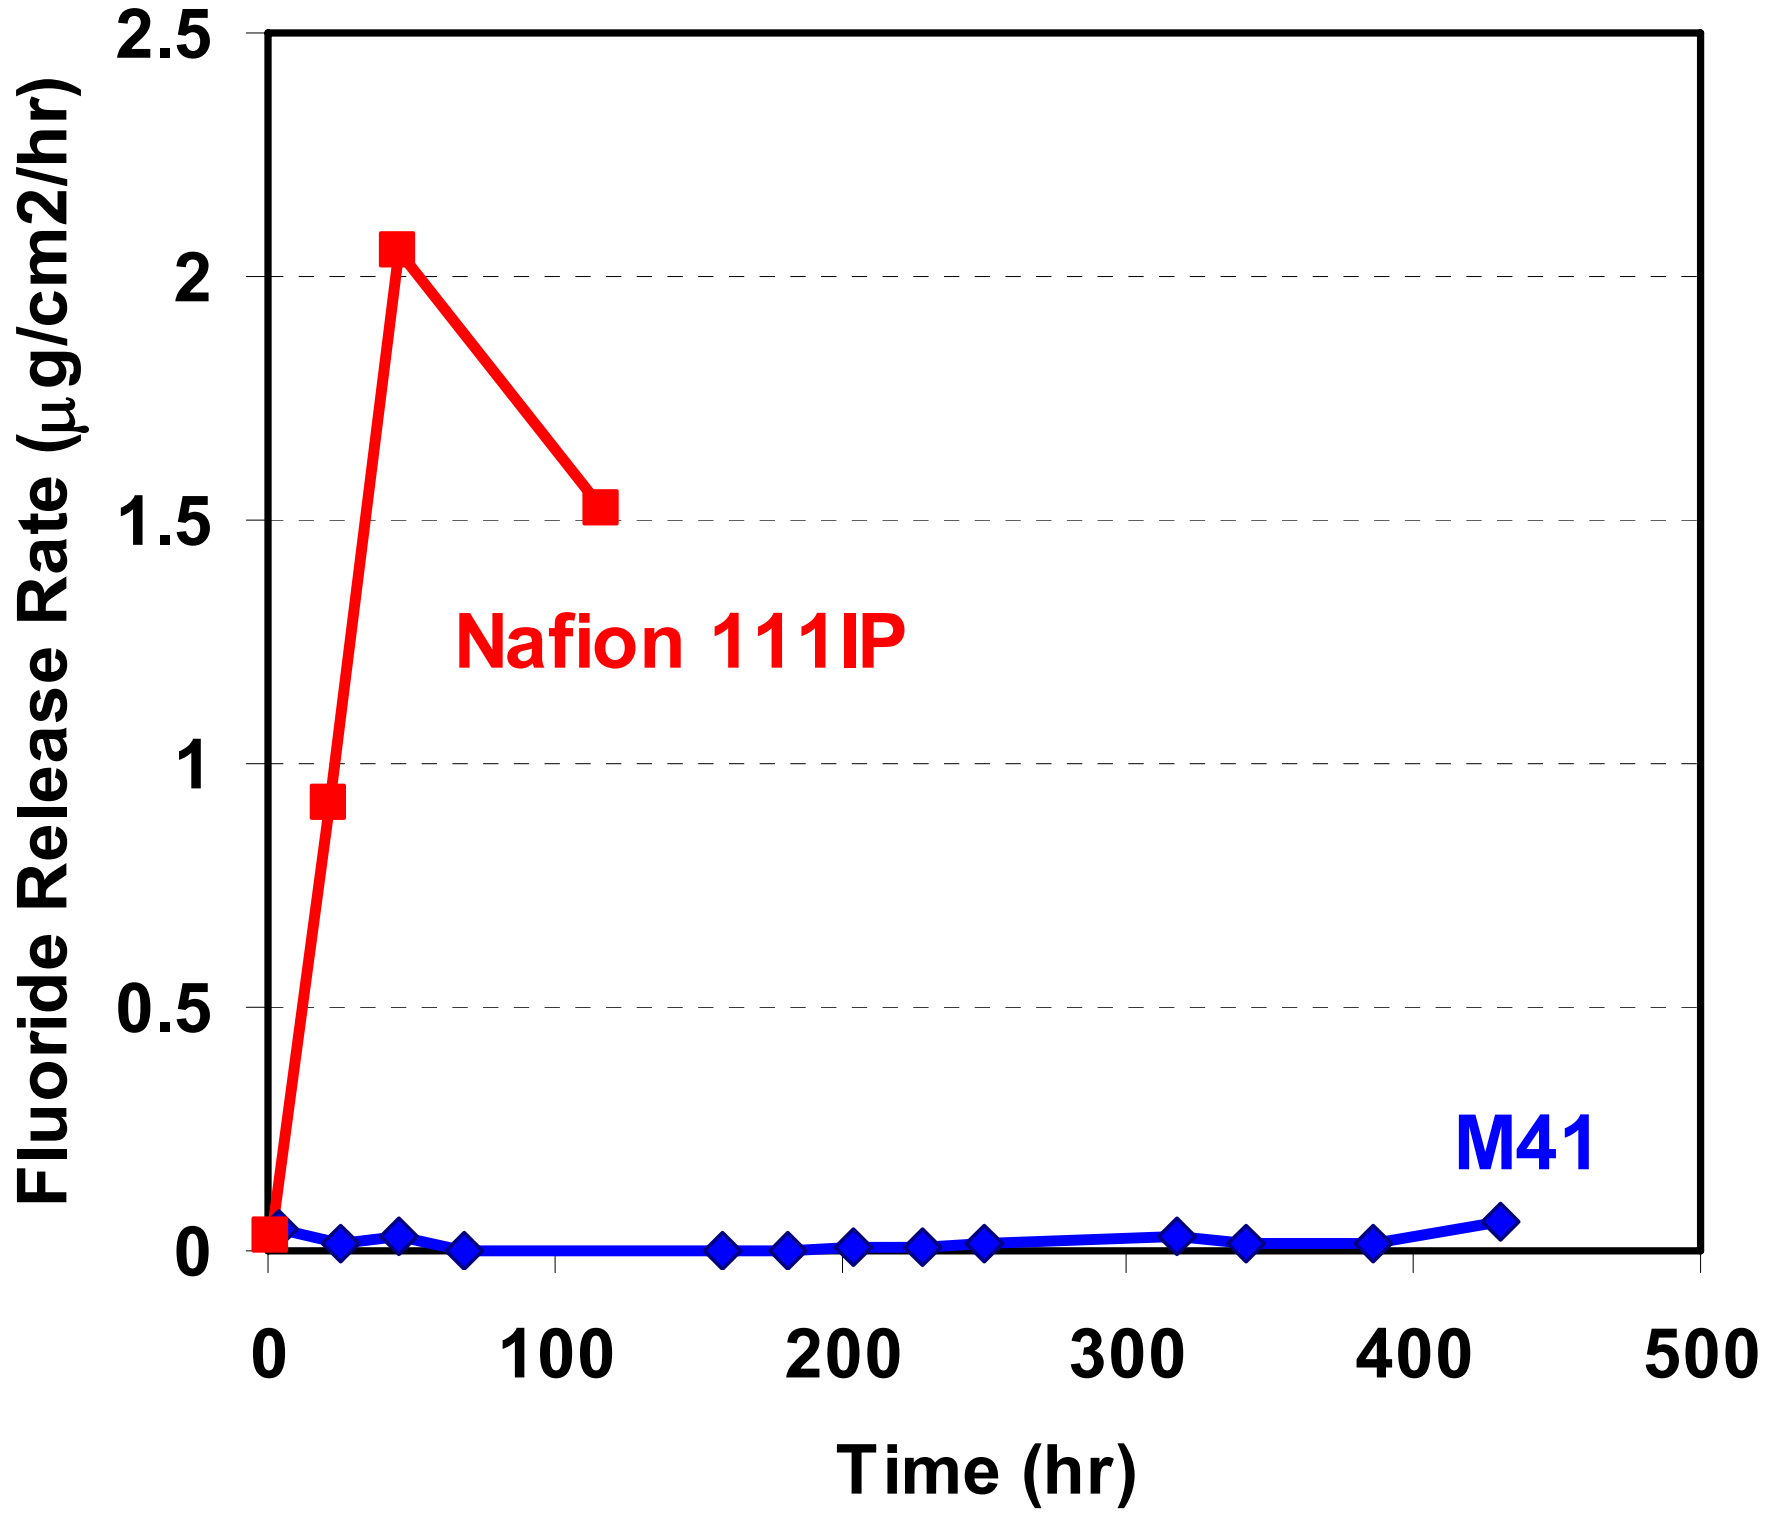

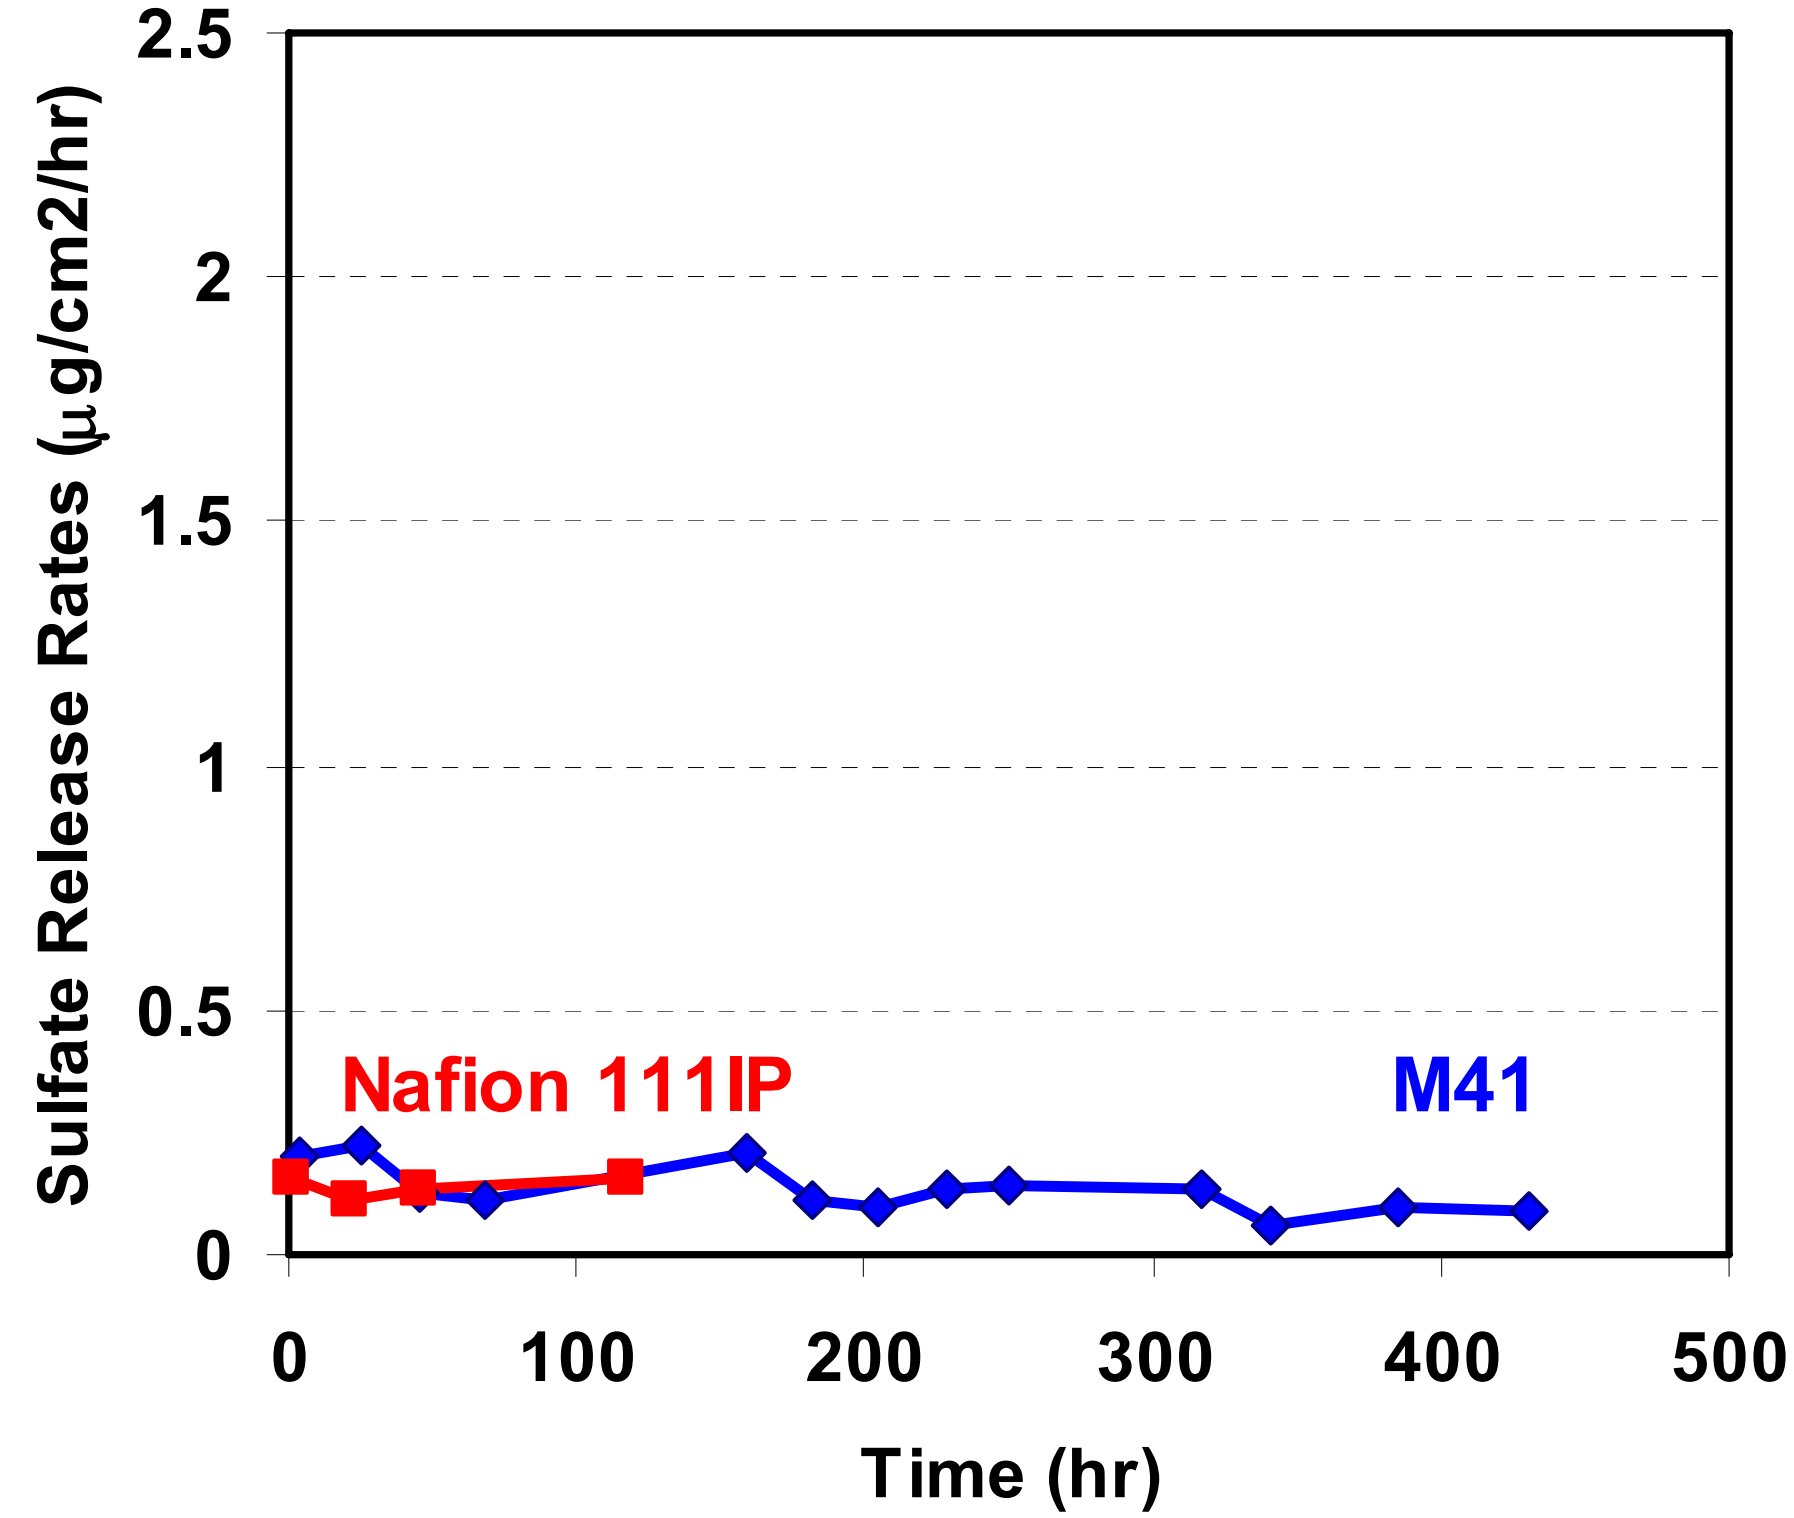

- M41 shows significantly lower fluoride release rates and similar sulfate release rates to Nafion® 111 membranes

M41 High Temperature Excursion Stability

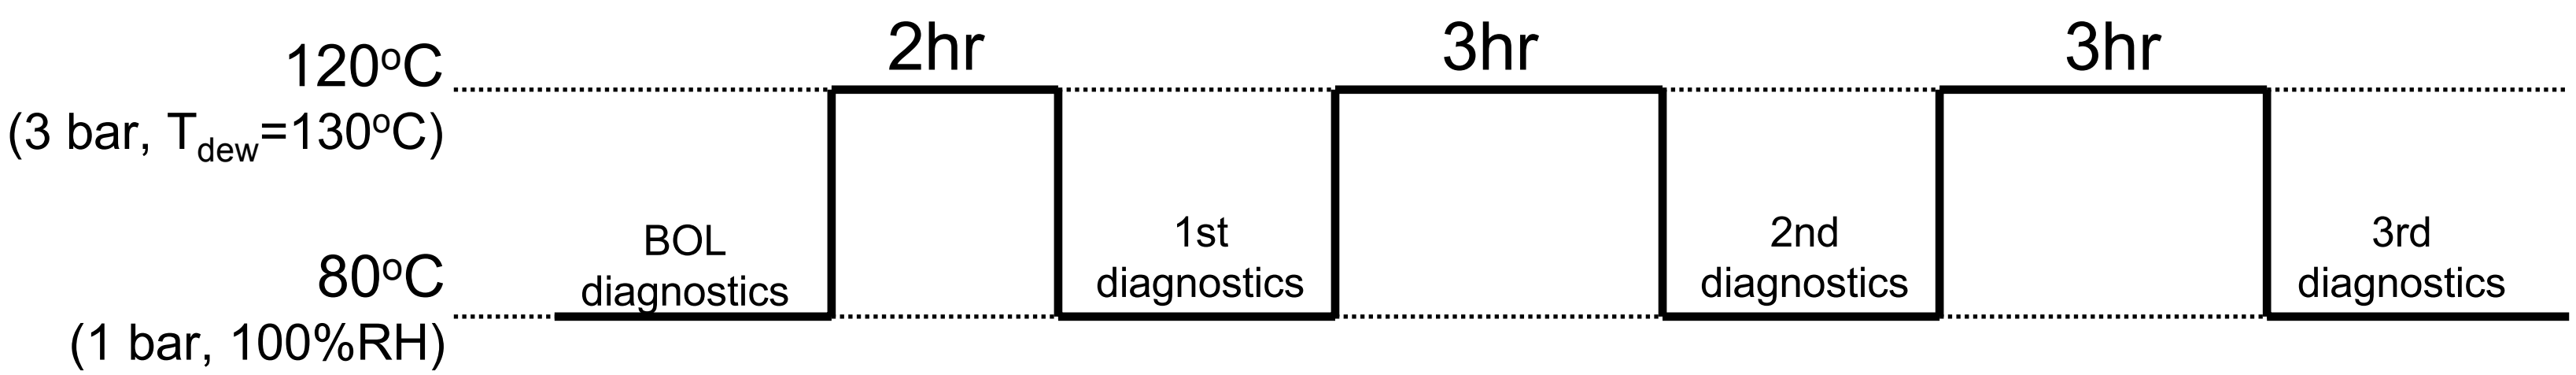

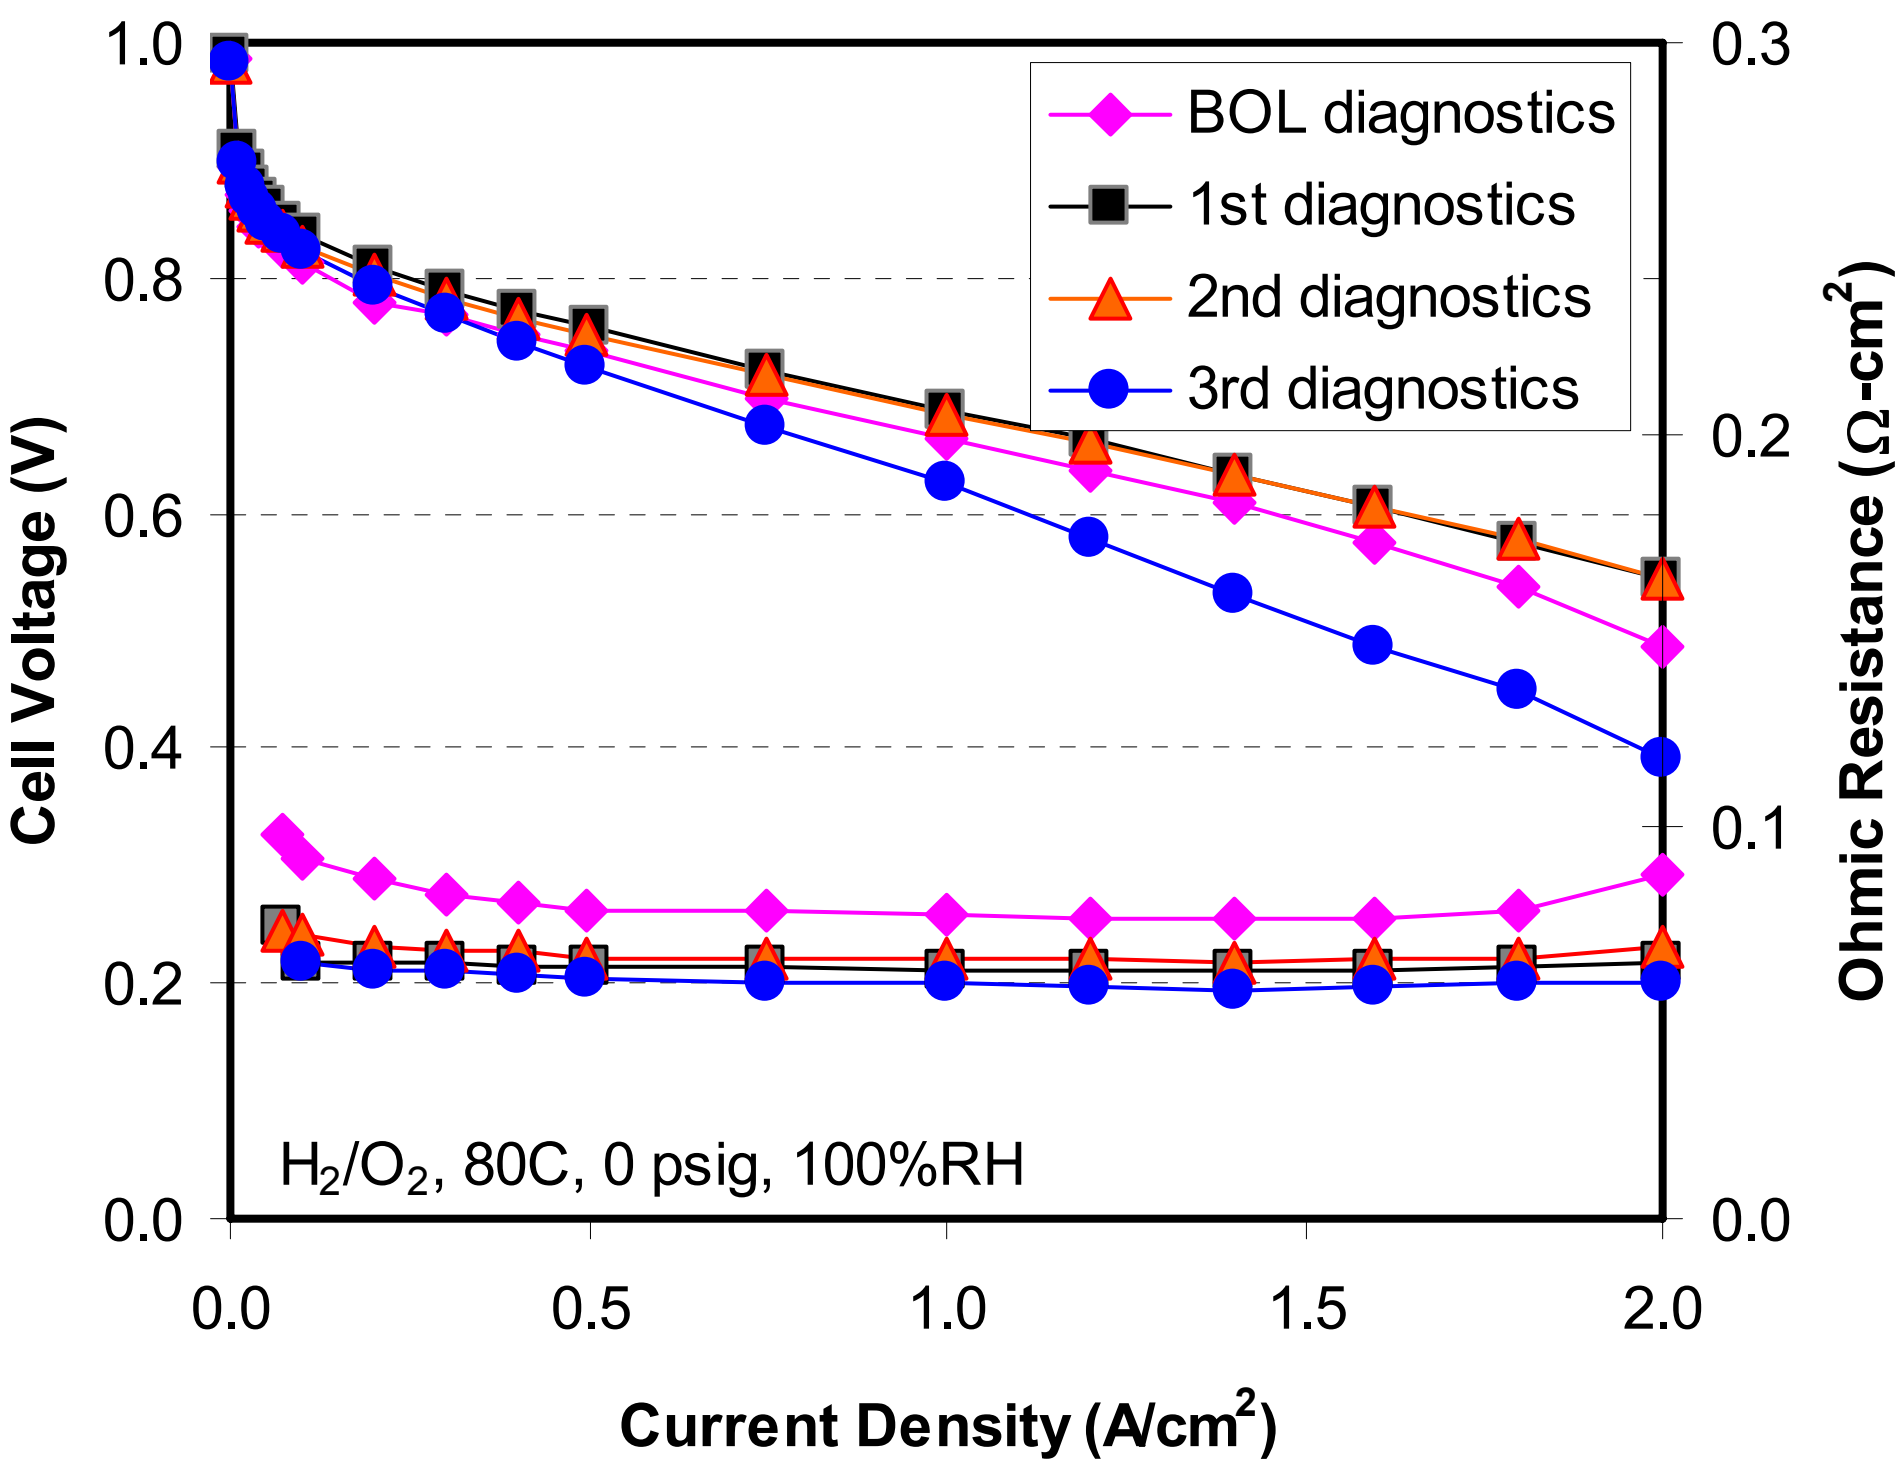

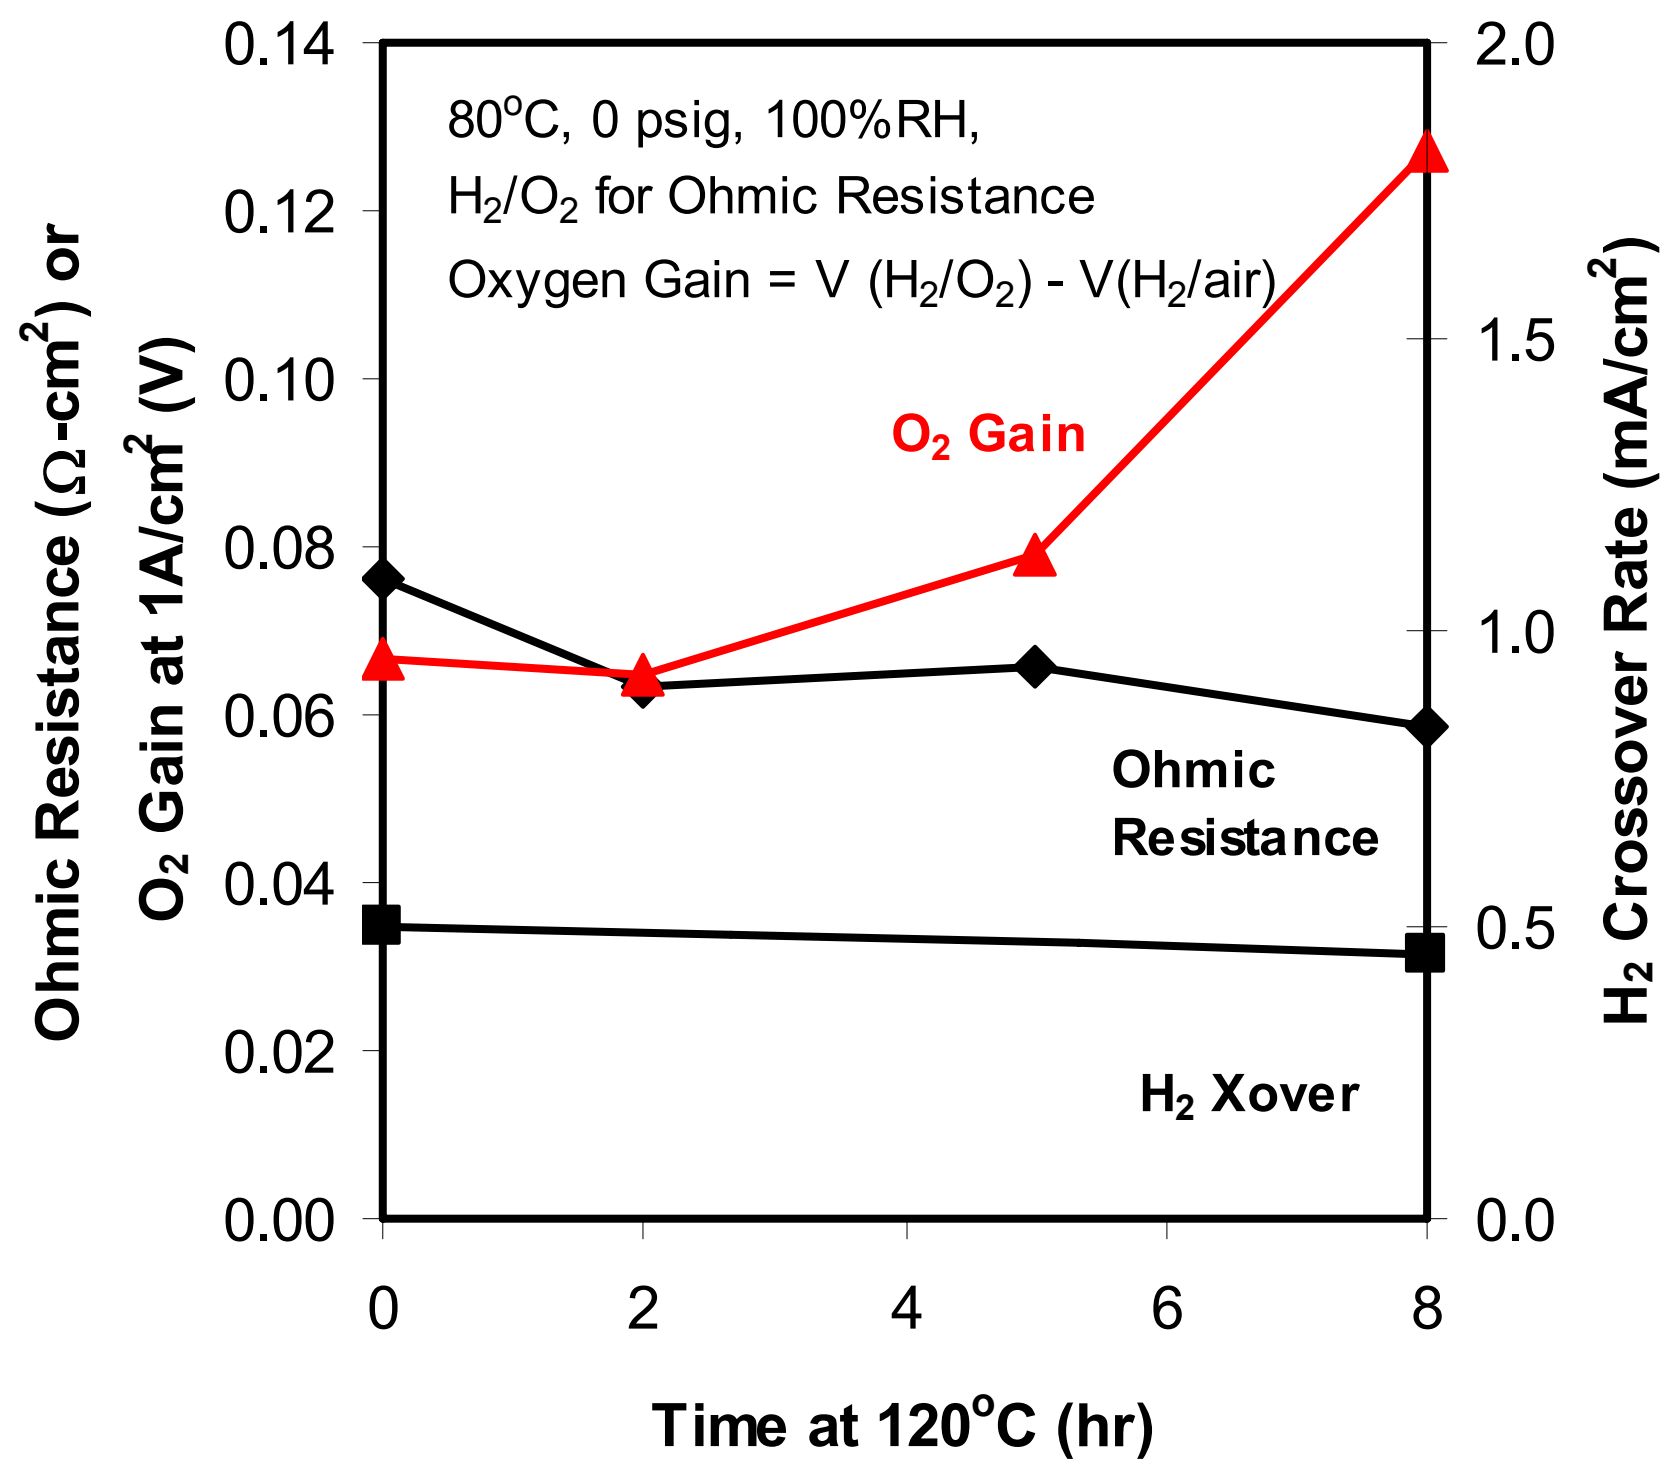

- Stable membrane performance is shown after 8 hrs at 120^oC
  - Electrode degradation is shown by higher O_2 gain and 20% loss of ECA

ARKEMA

Future Work

- This program is scheduled to begin 2Q2007

- Work for balance of FY07 and FY08
  - Develop new generation polyelectrolytes (Arkema & VPI)
    - Identify key target polyelectrolytes
    - Begin synthesis and *ex-situ* stability of new polyelectrolytes
    - Down select first candidates to carry into membrane development

  - Membrane development (Arkema)
    - Begin blending studies with down selected polyelectrolytes
    - Conduct *ex-situ* membrane testing to DOE targets

  - High-resolution morphology characterization for structure-property understanding (ORNL & Arkema)

Summary

- Arkema has developed a Kynar/polyelectrolyte blending technology capable of incorporating a wide variety of polyelectrolyte chemistries for producing fuel cell membranes

- An iterative process has been developed and used successfully to down select materials at early stages to speed the development cycle

- The latest membrane generation developed (M41) has demonstrated:
  - Equivalent fuel cell performance to Nafion® membranes
  - Better mechanical properties
  - Lower gas permeability
  - At least 4x increase in OCV durability versus Nafion® 111

- The technology and approaches already developed are fully applicable to the development of new membrane families with further improved performance at higher temperatures and lower relative humidities